

## Accepted Manuscript

Recent advances on first-principles modeling for the design of materials in CO<sub>2</sub> capture technologies

Yue Yuan, Huabei You, Luis Ricardez-Sandoval



PII: S1004-9541(18)31196-0  
DOI: <https://doi.org/10.1016/j.cjche.2018.10.017>  
Reference: CJCHE 1304

To appear in: *Chinese Journal of Chemical Engineering*

Received date: 9 August 2018  
Revised date: 3 October 2018  
Accepted date: 23 October 2018

Please cite this article as: Yue Yuan, Huabei You, Luis Ricardez-Sandoval , Recent advances on first-principles modeling for the design of materials in CO<sub>2</sub> capture technologies. Cjche (2018), <https://doi.org/10.1016/j.cjche.2018.10.017>

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

## Special Issue on Sustainable Chemical Product

Recent advances on first-principles modeling for the design of  
materials in CO<sub>2</sub> capture technologies

Yue Yuan<sup>1,2</sup>, Huabei You<sup>2</sup>, Luis Ricardez-Sandoval<sup>2\*</sup>

<sup>1</sup> Chemical Engineering Department, Tianjin University, Tianjin 300072, China

<sup>2</sup> Chemical Engineering Department, University of Waterloo, 200 University Ave W, Waterloo, ON N2L  
3G1, Canada

\*Corresponding author. E-mail: lricardezsandoval@uwaterloo.ca

**Abstract:** Novel technologies in consideration of industrial sustainability (IS) are in urgent need to satisfy the increasing demands from the society. IS realizes the production of materials and while maintaining environmental and resource sustainability. The chemical materials used in CO<sub>2</sub> capture and storage (CCS) technologies play a significant role in the disposal of greenhouse gas emissions coming from large stationary fossil-fired power plants, which breaks the principle of IS and brings severe environmental problems. This study aims at providing a detailed review of first-principles modeling (density functional theory, DFT) of materials in CO<sub>2</sub> capture technologies. DFT analysis provides insight into the atomic properties of the studied systems and builds an efficient guidance of the future design of the materials used in CO<sub>2</sub> capture technologies. Major materials including oxygen carriers, metal organic frameworks, membranes, zeolites, ionic liquids and some other promising candidates are considered. The computational studies bring the outcomes of the adsorption behaviors, structural characteristics and accurate force fields of the studied materials in short turn-around times at low cost. This review can stimulate the design of novel materials with specific target of CO<sub>2</sub> capture and promote the industrial sustainability of fossil fuel combustion technologies.

**Key words:** Industrial sustainability; CO<sub>2</sub> capture; Density Functional Theory; Fossil fuels

## 1. Introduction

With the continuous growth in human population, the demand for food, energy and fundamental living resources such as water has significantly increased. According to Godfray *et al.*[1], more than 14% of people in the world is still in hunger in this century; also, it is expected that by 2050 a growth in food supply from 70% to 100% will be needed to meet the population's demands. Industrial activities have also been increased to comply with the global demands. The increase in the industrial production of valuable goods has brought severe environmental problems and the inevitable drop in non-renewable resources such as fossil fuels. Therefore, the sustainability of the environment and resources is becoming a major global concern. In terms of industrial development, the production of valuable materials and products need to satisfy the increasing population demands; however, they need to do it in a sustainable way such that there is a balance between available resources and manufacture of valuable products. From an engineering perspective, the development of new green technologies can promote engineering sustainability, especially in consideration of industrial sustainability (IS). IS[2] refers to the transformation process including the industry that the overall production scheme contributes to a socially, environmentally and economically sustainable growth. Thus, IS requires industrial and academic practitioners to realize the industrial transformation process by taking into consideration economic, environmental and social aspects that enable the development and deployment of sustainable solutions. New materials and technologies are in urgent need to realize IS. The development and utilization of clean energies have become popular, e.g. wind, nuclear and solar energies [3],[4],[5]. In addition, the effect and treatment of industrial discharges are major considerations in terms of maintaining IS[6]. One aspect critical for the deployment of new (clean) technology in consideration of IS is the development, testing and implementation of advanced mathematical frameworks, which play a fundamental role to optimize chemical process sustainability and reduce their footprint on the environment [7],[8]. Among all the studies in the area of IS, the continuous growth in CO<sub>2</sub> emissions from fossil fuel combustion have attracted the most attention due to their environmental impact and global sustainability[9],[10].

According to the International Energy Agency (IEA) report in 2017[11], fossil fuel accounts for almost 80% of the overall energy supply in 2016, as shown in **Fig.1**.

Due to the current energy demands, fossil fuels are still not replaceable by renewables due to their relatively low costs and continuous development of efficient combustion technologies with near-zero emissions[12],[13],[14]. However, the environmental impact incurred when using fossil fuels during the combustion process has become a global issue that cannot be overlooked. Greenhouse gas effects are one of the most serious problems caused from the combustion of fossil fuels. Accordingly, environmental issues caused by greenhouse emissions do not comply with IS principles in modern manufacturing processes. Among all the greenhouse gas emissions, CO<sub>2</sub> represents almost 75% of greenhouse gases. One detrimental effect is that this gas has relatively long residence times, i.e., it remains in the atmosphere for long periods of time[15]. Thus, technologies aimed at reducing greenhouse emissions (mainly CO<sub>2</sub>) are key to curb global warming effects while still using fossil fuels for the large-scale production of power. One approach that can be considered to reduce CO<sub>2</sub> emissions to the atmosphere is through the deployment of technologies that can capture, store, manage and eventually utilize the CO<sub>2</sub> produced from large stationary sources such as fossil-fired power plants. The development of efficient CO<sub>2</sub> capture systems engaged with the continuous production of power from fossil fuels is attractive since it may drive the sustainable development of fossil-fired energy technologies with near-zero emissions. CO<sub>2</sub> disposal technologies are usually classified as pre-combustion, which reduces carbon capacity of fuels before combustion occurs; post-combustion (flue gases generated after combustion are cleaned); and oxy-fuel combustion, which makes use of pure O<sub>2</sub> as oxidizer. The process schemes of these CO<sub>2</sub> capture technologies are described in **Fig 2**.

Post-combustion is a relatively commercially mature technology which favors low pressure processes. However, the energy penalty of CO<sub>2</sub> separation while adopting post-combustion technologies (using e.g. amine-based solvents) is from 25 % to 40 % [16]. The post-combustion process normally operates at ambient pressure, low CO<sub>2</sub> concentrations (usually under 15%) and can often handle large flue gas flowrates. CO<sub>2</sub> partial pressure is usually less than 0.15 atm [17]. Pre-combustion technologies significantly reduces the energy consumptions associated with CO<sub>2</sub> capture, particularly in systems that operate at high pressures. Low temperatures such

as 40 °C are preferred to maintain the high efficiency in pre-combustion processes. According to a previous study[18], the energy penalty of the net plant efficiency in IGCC (Integrated Gasification Combined Cycle) plant with pre-combustion technology is from 7% to 9.5%. Compared to the pre and post combustion technologies, oxy-combustion usually adopts a recirculation process and lower the energy penalty through the separation of O<sub>2</sub> from air before combustion. A low mass flux and high CO<sub>2</sub> concentration of exhaust gas is expected to be separated in oxy-combustion. Despite its benefits, e.g. use of simple separation units to produce a highly pure CO<sub>2</sub> stream, this technology is still intensive and requires significant energy demands, mostly to separate O<sub>2</sub> from air. Despite the advances in carbon capture and storage (CCS) technologies, they usually sacrifice part of the overall system energy utilization efficiency to realize the CO<sub>2</sub> capture[19],[20],[21]. One key factor that affects the performance of CCS technologies is related to the type materials used to capture the CO<sub>2</sub>. Therefore, a large and diverse variety of potential materials need to be tested to evaluate its impact on both the efficiency to capture CO<sub>2</sub> and its corresponding energy costs for recovery. **Table 1** summarizes the most frequently used materials in pre-combustion, post-combustion and oxy-combustion processes. The applications of these materials to different CCS applications will be described in the subsequent sections in this study.

Computer aided design is key for the development and assessment of promising materials for CO<sub>2</sub> capture. It has been widely recognized that computer simulations at the atomistic and molecular scales can lead the development of new materials (or the optimal design of existing materials) in short turn-around times and at low cost[43] [44] thereby contributing to the sustainability of the environment and industrial processes. In particular, Density Functional Theory (DFT) analysis is a powerful atomistic (first-principles) modelling method used to screen out a large number of materials that can be employed for CO<sub>2</sub> capture. DFT is in the range of the quantum chemical methods and is widely used to predict the properties of chemical structures. To conduct a DFT analysis of different materials such as solvent, adsorption material and oxygen carriers (OCs), different models need to be used. For solid materials, the periodic vacuum slabs of the surface model[23],[45] are used to study the surface reactions while the isolated cluster models are usually employed to study particle interactions[46]. As for liquid solvents, the continuum solvation model (SMD) developed by Marenich et al.[47] can be used to study the CO<sub>2</sub> absorption into aqueous solutions [48]. DFT calculations are usually conducted at 0 K and vacuum

condition. The DFT energetic results can be adjusted to specific operating conditions using the atomistic thermodynamic models such as the ab initio atomistic thermodynamics [49],[50] or through molecular dynamic simulations. DFT analysis can provide insight into elementary reaction kinetics, charge distribution or transfer and microscopic morphological properties of systems under analysis. This modelling method has been proven to be a powerful tool to study the atomic behaviour of promising materials and provide significant guidance for the design of highly efficient (low-cost) materials for CO<sub>2</sub> capture.

In this work, we aim to review the most recent advances that have employed first-principles modelling (i.e. DFT) to advance our knowledge on the identification and atomistic design of suitable materials for CO<sub>2</sub> capture. This work focuses on the most common and promising materials used for the different CO<sub>2</sub> capture technologies such as oxygen carriers (OCs), Metal-Organic Frameworks (MOFs), membranes, zeolites and ionic liquids. Each type of materials will be reviewed in section 2. Recent advances in other materials such as porous carbons and amine solutions will also be discussed in section 2.6. A summary of the current state-of-the-art in materials for CO<sub>2</sub> capture will be provided at the end. The existing reports and challenges in DFT analysis of materials used in CO<sub>2</sub> capture will encourage further computational reports thus promoting IS in our society.

## 2. Materials in CCS

This section aims to present the recent advances in the commonly used and new chemicals used in the different CO<sub>2</sub> capture and storage technologies.

### 2.1 Oxygen carriers (OCs)

Chemical looping combustion (CLC) has attracted attention in the past decades due to its relatively low energy cost compared to other carbon capture and storage technologies[9],[51],[52],[53],[54],[55]. Based on the reaction properties, there are two types of chemical looping schemes that can realize the fuel conversion process. Type I CLC realizes the indirect combustion of fuels by introducing an oxygen carrier (OC), which minimizes the irreversible entropy during the combustion process. As shown in **Fig 3 (a)**, in the first reactor (the reducer), metal oxides are reduced to realize the full oxidation of either gas or solid fuels, e.g. syngas or coal. The reduced metal oxides are then transported into the second reactor (the combustor) to be

re-oxidized by air thus forming a loop. Through CLC, the combustion process is energy-effective since it simultaneously captures  $\text{CO}_2$  and produces heat thus promoting energy, environmental and ecosystem sustainability. As shown in **Fig. 3 (b)**, type II CLC also requires two reactors, i.e. a carbonator and a calciner, which includes  $\text{CO}_2$  transport using  $\text{CO}_2$  carriers. In the carbonator, CaO is carbonated by  $\text{CO}_2$  into  $\text{CaCO}_3$  whereas in the calciner the  $\text{CaCO}_3$  undergoes calcination reaction and release  $\text{CO}_2$  at high temperatures which increases the energy regeneration efficiency[56],[57]. Guo et al.[58] combined experimental and DFT methods to study the metal promoter (Al, Mg, Zr and Na) effect on CaO as OC. That study showed that Zr and Na benefit  $\text{CO}_2$  adsorption while Al and Mg weaken the adsorption. To the authors' knowledge, this is the only study of Ca-based OCs using first-principles (DFT) analysis.

Oxygen Carrier (OC) development is instrumental for the successful optimization and industrial-scale deployment of CLC technology. This material serves as an oxygen intermediate to combust fuels while energy is supplied by the redox reactions. High reaction reactivity for both the oxidation and the reduction processes is perhaps the most desired property for OC materials. In addition, large oxygen storage capacity facilitates fuel conversion. Moreover, to minimize the deactivation of OCs, high mechanical strength and long-term stability under severe operational conditions are desired (20 bar, around  $1000^\circ\text{C}$ [59],[60]). Furthermore, OCs should be inexpensive, easy to access and should not lead to serious environmental concerns. Numerous OC materials have been experimentally studied and tested over the past decades[61]. Compared to experimental studies, first-principles modeling studies for OCs are relatively limited. DFT, as well as other quantum chemistry methods, have been popular tools used to provide insight on elementary reaction kinetics[62],[63],[64],[65]. DFT analysis has been mostly employed in this field to study the reactivity of OCs in the redox process. In terms of OC development for CLC applications using DFT analysis, iron-based materials are the most widely studied materials[22],[66],[67] followed by Cu-based OCs[68]. Though NiO-based is one of the most popular OCs in CLC, only a limited number of DFT studies for NiO has been conducted[69],[70]. Theoretical studies focused on other metals are rather scarce in the literature.

Dong *et al.*[22] conducted a DFT analysis on  $\text{Fe}_2\text{O}_3$  as OC using CO as a gas fuel. That study showed that  $\text{Fe}_2\text{O}_3$  (1102) surface has higher reaction activity with CO than  $\text{Fe}_2\text{O}_3$  (0001) surface. In another study conducted by the same group, they

reported that high index surface  $\text{Fe}_2\text{O}_3$  (104) performs better than low index (001) surface[71]. Carbon deposition[72] and mercury adsorption[73] were also investigated by the same group to assess the impurity effects on the  $\text{Fe}_2\text{O}_3$  surface. Methane decomposition mechanisms on  $\text{Fe}_2\text{O}_3$  have been studied using DFT by multiple groups. Different reaction pathways have been established on  $\text{Fe}_2\text{O}_3$  surfaces[74],[75],[76]. Due to the complexity of methane decomposition paths, this reaction mechanism is still under debate and will likely be the subject of future research studies in this area. In a different study, Fan *et al.*<sup>9</sup> considered the oxygen vacancy on  $\alpha\text{-Fe}_2\text{O}_3$  (001) surface, which has been shown to enhance the partial oxidation of  $\text{CH}_4$ . Other fuel molecules reacting on the  $\text{Fe}_2\text{O}_3$  surface have been investigated such as carbon atoms or CO[77],[78]. Those DFT studies reported the reaction kinetics in a solid fuel CLC process. Supports such as  $\text{Al}_2\text{O}_3$ ,  $\text{ZrO}_2$  and  $\text{MgO}$  have also been studied as the inert support of  $\text{Fe}_2\text{O}_3$ [66],[79],[80].  $\text{ZrO}_2$  supported  $\text{Fe}_2\text{O}_3$ [66] and  $\text{MgO}$  supported  $\text{Fe}_2\text{O}_3$ [80] were investigated by Tan *et al.* Those studies showed that  $\text{ZrO}_2$  could enhance the adsorption of CO while  $\text{MgO}$  lowered the reaction barriers of CO oxidation compared to the pure  $\text{Fe}_2\text{O}_3$  OC.

Cu-based OCs are promising materials for the oxygen uncoupling (CLOU) process since  $\text{O}_2$  is released in the reducer. The support effect on the sintering resistance of CuO was studied by Zhao *et al.* [81]; four supports ( $\text{TiO}_2$ ,  $\text{ZrO}_2$ ,  $\text{CuAl}_2\text{O}_4$  and  $\text{MgAl}_2\text{O}_4$ ) were studied and all the supports were shown to reduce the energy barriers of the fuel combustion process. Among them,  $\text{CuAl}_2\text{O}_4$  showed the best performance in the CLOU process. A specially synthesized Cu-based OC with a core ( $\text{Al}_2\text{O}_3$ )-shell ( $\text{TiO}_2$ ) support was studied by Xu and Zhao[82]. That study showed that this material could effectively prevent the impurity formation in CLOU process. Studies involving graphene[83] and  $\text{ZrO}_2$ [84] supports have also been reported and have shown that graphene improves the reaction activity of OC with CO whereas  $\text{ZrO}_2$  contributes to the CO oxidation. Liu *et al.*[85] showed that Zr benefits the oxygen vacancy formation and migration on CuO surface which leads to higher reactivity of CuO as OC.

NiO (001) perfect and defective surfaces have been considered in DFT studies for CLC applications. A report by Cai *et al.*[23] has shown that the oxygen vacancy on NiO enhanced the  $\text{O}_2$  dissociation in the reduction process. The impurity of CLC ( $\text{H}_2\text{S}$ ) on NiO (001) perfect and defect surfaces was studied by Guo *et al.*[86]. The results from that DFT study showed that impurity may notably reduce the CO adsorption on the surface. The oxidation process of Ni in CLC was also studied using

DFT[87]. Other OCs like  $\text{Mn}_3\text{O}_4$  (001) [88] and  $\text{CaSO}_4$  [89] have also been investigated in CO and  $\text{CH}_4$  conversions, respectively. Those works have provided the elementary reaction kinetics of the studied systems. Theoretical studies on supports of NiO are limited even for the most common  $\text{Al}_2\text{O}_3$  supported NiO.

Mixed OCs which contain more than one metal elements have attracted much attention as OCs. Studies focusing on perovskites such as  $\text{BaMnO}_3$  and  $\text{SrMnO}_3$  have been reported. Results from those studies have shown that different compositions of those materials have resulted in different reaction activity performances[90],[91]. Note that Fan *et al* [24] reported a DFT analysis combined with experimental data that studied the role of metal oxide support. In that work, the structure of ilmenite ( $\text{FeTiO}_3$ ) has been chosen to represent the  $\text{TiO}_2$ -supported iron oxide. That study presents a comprehensive understanding of the  $\text{TiO}_2$  support effect on iron-based OC and provides a representative demonstration of DFT study in this area. Since  $\text{FeTiO}_3$  is the active component of ilmenite while it also contains MgO and  $\text{Al}_2\text{O}_3$ [92], that study can be used as a basis to develop a new study of trace metal elements in ilmenite as mixed OCs.

In summary, CLC is an energetically favorable process with inherent  $\text{CO}_2$  separation characteristics that can significantly contribute to curb greenhouse gas emissions. To enhance CLC performance, DFT analysis of OCs will provide the fundamental atomistic understanding of the studied systems. However, DFT simulation reports of Ni-based OCs[23] as well as the other materials, natural ores for instance, are limited in the literature. Furthermore, some significant topics such as lattice transfer performance for OCs using DFT analysis have not been reported in the literature. To screen and design promising OCs without too much cost, further DFT-based studies are needed.

## 2.2 MOFs

Metal-organic frameworks (MOFs) are one of the most promising adsorbents of  $\text{CO}_2$  capture and have become the main focus of research for many experimental and theoretical studies. MOFs are highly ordered crystals containing both metal nodes (metal ions or metal clusters) and organic linkers, which enable MOFs to have a wide variety of properties for multiple applications[93]. The diversity of MOFs, different metal sites and different linkers, leads to the need for a large scale screening of these materials using atomistic (DFT) methods. As adsorbents, MOFs are known for their high pore volume, high surface area and internal surface (higher than  $7,000 \text{ m}^2/\text{g}$ ) [94]. Also, physical and chemical properties of MOFs such as pore size or functional

groups can be tailored by choosing different building blocks and synthesis strategies[95]. The methods to synthesize MOFs have been the focus of multiple studies in this area since they can potentially tune desirable characteristics for MOFs[93]. As for the materials' strength, structures of MOFs have high robustness, which means that the adsorbed species can be removed to realize the activation of adsorbents while maintaining the crystal structure of MOFs. All the characteristics described above make MOFs promising candidates for CO<sub>2</sub> capture adsorbents for post-combustion technologies, which have been tested through multiple experimental and simulational studies[96],[97],[98].

One area of research in MOF is focused on coordinatively unsaturated sites (CUS), which tend to form reversible bonds with CO<sub>2</sub>[94]. The most popular potentials used to simulate the interactions between CO<sub>2</sub> and MOFs, i.e., a combination of Lennard-Jones (LJ) potential and Coulombic potentials[99], cannot accurately predict the adsorption properties since those potentials have been mostly developed for physical adsorption processes. Therefore, first-principles based force field studies are popular to analyze and evaluate the capabilities of MOFs to adsorb CO<sub>2</sub> [100],[101]. DFT analysis on MOFs can also provide lattice constants and atomic geometries as well as particle properties during the gas adsorption process, e.g. mechanics of adsorption, particularly for CO<sub>2</sub> capture[102]. Computer-aided design allows efficient and fast screening of MOFs for CO<sub>2</sub> capture. The aim of this section is to review those recent modelling studies that have considered the adsorption properties of MOFs for CO<sub>2</sub> such as adsorption, selectivity and impurity effects. Also, a summary of the optimization strategies to improve CO<sub>2</sub> separation process by MOFs is described. DFT-based force fields, which are constructed to simulate the expected behavior of MOFs in the CO<sub>2</sub> capture process, will be described at the end of this section.

In the selection of adsorbents to capture CO<sub>2</sub>, the adsorption properties such as adsorption capacities and CO<sub>2</sub> selectivity are usually key for the identification of a promising solvent. Ramsahye *et al.*[103] calculated the charge distribution of the MIL-53 by DFT analysis. Periodic models as well as cluster models of MIL-53 were employed and have shown to achieve good agreement with structures observed from experiments. The charge distribution predicted from DFT simulations was used to simulate a grand canonical Monte Carlo (GCMC) model, which is the most commonly used simulation method in this area. Then the adsorption capacity, as well as selectivity of CO<sub>2</sub>, were estimated. That work showed that the Mulliken charges

from periodic models are more transferable between the two changing structures of MIL-53 due to its flexibility, which would provide a better prediction for the entire adsorption process. Hu *et al.*[104] showed that Zr-BFDC (O-heterocyclic ligand contained) performed the best among three studied UiO-type of MOFs. MOFs have been simulated in numerous studies and shown to be promising CO<sub>2</sub> adsorbents with high adsorption capacity and easy to regenerate. Borges *et al.*[105] reported a study focused on selectivity of CO<sub>2</sub> capture among H<sub>2</sub>, N<sub>2</sub>, CH<sub>4</sub> and CO. That study indicated that MIL-160 was a promising adsorbent of selective CO<sub>2</sub> adsorption. The adsorption mechanism (i.e. the binding energies of CO<sub>2</sub>) was obtained from DFT analysis. The results from that work showed that CO<sub>2</sub> tends to be adsorbed on the Zr-metal cluster. Liu *et al.* reported[106] that the side position where the CO<sub>2</sub> is closer to the hydrogen side of the organic linker is the most favored site among multiple configurations. DFT has been shown to be an effective tool for the prediction of adsorption mechanism in MOF-contained systems. Impurity effects on the CO<sub>2</sub> adsorption process can also be obtained from DFT simulations. Yu *et al.*[107] simulated the CO<sub>2</sub> adsorption using Mg-MOF-74 in a system that contained water. The water-coordinated MOF has lower binding energy with CO<sub>2</sub>, which leads to a decrease in the adsorption capacity of CO<sub>2</sub>. Regarding the functional group effects, Torrisi *et al.*[97] reported four functionalized MIL-53 containing different groups (OH-, COOH-, NH<sub>2</sub>- and CH<sub>3</sub>-). The results reported that each functional group have different favored adsorption sites and bonding energies. Functional groups (especially OH- and COOH-) have enhanced the adsorption of CO<sub>2</sub> by MIL-53 in consideration of capacity of CO<sub>2</sub> and the selectivity of CO<sub>2</sub> over CH<sub>4</sub>.

The computational studies mentioned above provide guidelines for the optimization of MOFs or even the design of new MOFs for CO<sub>2</sub> capture. Unsaturated sites, polar functional groups, alkylamine incorporation and pore size can contribute to CO<sub>2</sub> capture with MOFs[94]. Nazarian *et al.*[108] analyzed 879 MOFs which structures were optimized using DFT analysis. In some cases, the computationally optimized structures make the CO<sub>2</sub> adsorption significantly different from the experimental results; the major source of discrepancy was due to the use of force fields that were not able capture the key characteristics of the system; therefore, the development of accurate force fields for those systems is indeed needed to further advance the design of new MOFs materials. In terms of force field development for MOFs, DFT calculations can optimize the structures of the studied materials such as the surface model or the isolated cluster configurations. Also, the interactions and

distances between the particles can be obtained by DFT analysis as well as the energetic and electronic properties of the configurations. These results are then used in the specific force field models such the 12-6 Lennard-Jones potential. Grand Canonical Monte Carlo (GCMC) simulations can be used to validate the force field models by comparing the GCMC predictions with experimental observations [109]. Especially for the MOFs with open metal sites, general force fields such as UFF (Universal force field)[110] cannot accurately simulate the adsorption behavior since they cannot predict the strong interactions present between CO<sub>2</sub> and the adsorbent containing open sites. As mentioned above, CUM contained MOFs has been widely studied using DFT analysis given that the open metal site has the potential to form a chemical bond with CO<sub>2</sub>. Haldoupis *et al.*[111] reported that the favorable adsorption sites of CO<sub>2</sub> are the existing open metal sites of the studied M-MOF-74 (M stands for Mn, Co, Ni, Cu). Also, they parametrized the interactions between CO<sub>2</sub> and the unsaturated sites using the DFT-derived interaction energy. The developed force fields were able to predict consistent adsorption isotherms that agree well with previous experimental results. Poloni *et al.* [112] studied MOF-74 (Ca and Mg) as well as BTT-type MOFs containing unsaturated sites (BTT stands for 1,3,5-benzenetristetrazolate). That study showed that binding energies are highly sensitive to the existing divalent cations in BTT; similarly, the open V and Ti sites favored the CO<sub>2</sub> adsorption in M-MOF-74.

Another research avenue in MOFs is the simulation of breathing MOFs, i.e. MOFs with flexible structures like MOF-5. Adequate force fields that can predict flexible MOFs are currently under investigation [113]. Zhao *et al.*[25] performed a DFT analysis to obtain the angle bending parameters around Cu of Cu-BTC (Cu<sub>3</sub>(BTC)<sub>2</sub> with BTC (benzene-1,3,5-tricarboxylate), which is a breathing MOF. The new force field, which was developed to describe the breathing MOF, Cu-BTC, combined parameters estimated from DFT and slightly modified existing parameters, i.e. the intramolecular force constants from a widely used CVFF (Consistent Valence Force-Field) [114],[115]. The new force field is evaluated by its prediction of Cu-BTC crystal structures, adsorption behavior, etc. According to the comparison of the experimental outcomes and simulated results, the newly developed force field can give an accurate prediction of the properties of Cu-BTC such as the crystal structure, vibrational properties and the adsorption behavior.

DFT analysis can provide the characteristics of MOFs such as lattice parameters of MOFs, which can lay a solid foundation for future structure-relation studies of CO<sub>2</sub>

capture using MOFs. Also, the development of new force fields improve the accuracy of the simulational outcomes and extend the systems that can be explored using DFT analysis.

### 2.3 Membranes

The application of membranes in CO<sub>2</sub> capture mainly includes H<sub>2</sub>/CO<sub>2</sub> separation for pre-combustion, CO<sub>2</sub>/N<sub>2</sub> separation for post-combustion and O<sub>2</sub>/N<sub>2</sub> separation for oxy-fuel combustion. Membranes act as filters in the separation process since they only allow targeted components in the gas mixtures to permeate through, while leaving the rest of the species behind, which produces a pure stream of the desired gas component. Membrane-based technology has shown great potential in CCS since it does not require significant investment in large-scale power plant facilities. Also, this technology is not energy intensive like the traditional solvent-based technologies, which require large amounts of heat to regenerate the solvent. Moreover, membranes only need to be replaced when they reached their life span. Depending on their specific configuration, membranes can also be designed to suit the different needs for the separation processes.

The design of a membrane for CO<sub>2</sub> capture is mostly driven by the permeability and selectivity of the membrane. Permeability represents the gas permeation flux per unit pressure, whereas selectivity denotes the ratio of the permeabilities among different gas species. Membranes used for CO<sub>2</sub> capture are typically classified as: inorganic frameworks (*e.g.* metallic, carbon, silica, zeolite and metal-organic frameworks[116]); and organic frameworks, which mainly includes cellulose acetate and polymers[117].

Considering the number of different frameworks and possible configurations that can be employed to build a membrane, measuring the performance of the different membrane candidates under a wide range of operating conditions in a laboratory is not only time-consuming, but also expensive. On the other hand, computational simulations can be used for screening and identification of the most promising structures for different applications. In what follows, we will discuss the first-principles calculation studies on membranes that are H<sub>2</sub> selective, CO<sub>2</sub> selective, and N<sub>2</sub> selective respectively.

H<sub>2</sub> selective membranes are mainly used in pre-combustion CO<sub>2</sub> capture process to separate a mixture of H<sub>2</sub> and CO<sub>2</sub> at high pressures and temperatures. Metal membranes are to a certain extent ideal for this type of processes because of their

potential infinite H<sub>2</sub> selectivity[118]. Hydrogen purification membranes made of Palladium (Pd) and its alloys have been heavily studied over the past 50 years[28]. The main drawback of pure Pd-based membranes is that they are prone to surface contamination and H<sub>2</sub>-induced embrittlement at temperatures below 300 °C. On the other hand, Pd-alloy membranes have the potential to resist surface poisoning while maintaining desirable properties of pure Pd membrane. Kamakoti *et al.*[119] used plane wave DFT calculations to examine the binding energy and diffusion activation energies for dilute interstitial H in pure Pd, bcc and fcc CuPd alloys with ~ 50 at.% Pd. The dilute interstitial hydrogen loading was approximated by placing a single H atom on each of the compound's computational supercells. The diffusion activation energy was calculated using harmonic transition state theory (TST) with zero-point corrections. Results from this study have shown that H atom has the strongest binding energy with pure Pd, which also has the smallest net activation energy for H diffusion. As an indicator of the calculation accuracy, the predicted H diffusion activation energy in pure Pd (0.24 eV) was found to be in excellent agreement with experimental results (0.23 eV). Ling *et al.*[120] applied DFT-based calculation to evaluate the interactions between H<sub>2</sub> and a wide range of compositions of PdCuAg alloy membranes. DFT calculation was employed to obtain the hydrogen solubility, diffusivity, and permeability of each composition examined. A contour map was generated as a function of the alloy composition based on a large collection of DFT results. That study concluded that the solubility of hydrogen increases with Ag concentration while this variation can also cause a decrease in the diffusivity. Specific compositions that have a higher permeability than pure Pd have also been identified. Chandrasekhar *et al.*[121] calculated hydrogen solubility for 78 Pd-based binary intermetallics and used this information as a screening parameter to generate a shorter list of candidates to study hydrogen permeability. The study revealed that no material has higher hydrogen permeability than pure Pd. However, their work significantly increases the set of materials for which hydrogen permeability is known.

Carbon-based membranes separate H<sub>2</sub> from gas mixtures by molecular sieving. Zhang *et al.*[122] calculated the H<sub>2</sub> permeability and selectivity of sp-sp<sup>2</sup> hybridized carbon allotrope membranes with different natural pores, *i.e.*, graphyne, graphdiyne, and rhombic-graphyne. Their calculations showed that these properties are highly dependent on the pore sizes and membrane shapes. Among all the structures, rhombic-graphyne showed the largest discrepancy in penetration energy barrier for different gas molecules (0.54, 1.55, 1.73, and 3.00 eV for H<sub>2</sub>, CO, N<sub>2</sub>, and CH<sub>4</sub>

respectively); this promotes high H<sub>2</sub> selectivity ( $>10^{16}$ ) while maintaining a reasonable H<sub>2</sub> permeability. Wang *et al.* proposed four differently modified graphene membranes with H-deactivated pores (HP6, HP10, HP13, and HP16) and investigated their abilities to separate H<sub>2</sub> from gas mixtures (See **Fig. 4**)[29]. In that study, DFT-based calculations were performed to obtain the permeation energy barriers of each gas species (H<sub>2</sub>, CO, N<sub>2</sub>, and CH<sub>4</sub>). It was found that H<sub>2</sub> has the lowest permeation energy barriers on all four pore structures studied. Among all membranes examined, HP6 membrane exhibited the highest H<sub>2</sub> selectivity followed by HP10. However, large permeation energy barriers of H<sub>2</sub> have also been observed on HP6 and HP10 membranes (13.64 kcal/mol for HP6 and 7.05 kcal/mol for HP10); these results suggest low gas permeabilities. As for HP13 and HP16, the H<sub>2</sub> permeation energy barriers are very small and can result in high permeabilities (0.52 kcal/mol on HP13 and 0.03 kcal/mol on HP16). However, the calculated energy barriers of CO on HP13 (1.06 kcal/mol) and HP16 (0.94 kcal/mol) are not significantly higher than those obtained for H<sub>2</sub>, which can lead to poor selectivity of H<sub>2</sub> over CO. On the other hand, HP13 and HP16 can be used to separate H<sub>2</sub> from CO<sub>2</sub> and CH<sub>4</sub> with the selectivity of  $4.6 \times 10^3$  (HP13) and  $4.3 \times 10^2$  (HP16) for H<sub>2</sub>/CO<sub>2</sub> mixture; and the selectivity of  $5.4 \times 10^8$  (HP13) and  $1.1 \times 10^4$  (HP16) for H<sub>2</sub>/CH<sub>4</sub> mixture. These results indicate that H-deactivated graphene could be a promising material for H<sub>2</sub> selective membranes.

CO<sub>2</sub>-selective membranes are mainly used in post-combustion CO<sub>2</sub> capture process to separate a mixture of N<sub>2</sub> and CO<sub>2</sub>. Cazorla *et al.*[123] calculated the CO<sub>2</sub> selectivity and capacity of the Calcium-decorated carbon nanostructures using DFT analysis. In their work, the Perdew-Burke-Ernzerhof generalized gradient approximation (PBE-GGA) for the exchange-correlation energy was employed. The calculated binding energy of N<sub>2</sub> is much smaller than CO<sub>2</sub> on the Ca-doped surface ( $E_{\text{bind},\text{N}_2} = -0.645$  eV and  $E_{\text{bind},\text{CO}_2} = -2.731$  eV on  $X_{\text{Ca}} = 12.4\%$  graphene surface). Also, the formation of calcium carbonate (CaCO<sub>3</sub>) promoted CO<sub>2</sub> selectivity. These results suggest that Ca-decorated carbon nanostructure membranes are suitable for their applications in post-combustion technologies. Ostwal *et al.*[124] used DFT calculations to investigate the means of CO<sub>2</sub> hopping on the 3-aminopropyl-triethoxy silane (APTS) functionalized silica membrane. The binding energy of CO<sub>2</sub> adsorption (15.5 kcal/mol) and the activation energy of CO<sub>2</sub> diffusion/hopping from one amine group to another of APTS (7.2 kcal/mol) were in good agreement with experimental results (14.33 - 21.5 kcal/mol and 8.0 kcal/mol, respectively). Therefore, CO<sub>2</sub>

molecules are likely to follow the proposed mechanism when they interact with the APTS membrane. Wu *et al.*[125] also performed DFT-based simulations to investigate the mechanism of the fluorine-modified porous graphene membrane for CO<sub>2</sub>/N<sub>2</sub> separation. Their result showed that the pore-22 graphene (with 22 carbon atoms drilled out) has small diffusion energy barriers for both CO<sub>2</sub> and N<sub>2</sub>, which leads to a low selectivity. However, once the fluorine has been modified, the diffusion barrier for CO<sub>2</sub> decreased to 0.029 eV, while the diffusion barrier for N<sub>2</sub> increased to 0.116 eV. This difference suggests that CO<sub>2</sub> will pass through the membrane much easier than N<sub>2</sub>, thus enhancing the selectivity of CO<sub>2</sub>/N<sub>2</sub> mixture. Watanaba *et al.*[30] predicted the capability of a MOF material Cu(hfipbb)(H<sub>2</sub>hfibpp)<sub>0.5</sub> (H<sub>2</sub>hfipbb = 4,4'-(hexafluoroisopropylidene)-bis-(benzoic acid) for membrane-based CO<sub>2</sub>/CH<sub>4</sub> separation. In their work, DFT calculations were used to confirm the significant difference between the diffusion energy barriers of CO<sub>2</sub> and CH<sub>4</sub>. The diffusion activation energies of CO<sub>2</sub> and CH<sub>4</sub> in the pore of Cu(hfipbb)(H<sub>2</sub>hfibpp)<sub>0.5</sub> were calculated using TST. According to their calculations, the activation energies for CH<sub>4</sub> and CO<sub>2</sub> are 45 kJ/mol and 16 kJ/mol respectively, which justifies the high CO<sub>2</sub> selectivity exhibited by this material. DFT calculations has also been used to provide geometry optimized structures [126] or force constants and atomic charges that can be used to develop force fields (FFs) for molecular dynamic simulations [127] (See Section 2.2).

The concept of a N<sub>2</sub>-selective membrane stems from the development of H<sub>2</sub>-selective metallic membranes. Rochana *et al.*[128] studied the molecular dissociative adsorption of nitrogen and potential subsequent atomic diffusion within the Vanadium (110) surface and alloys with Ruthenium (Ru). That report showed that the binding energy of N<sub>2</sub> and atomic nitrogen bind on the V (110) surface is stronger than that of the Fe surface, which is traditionally used as the catalyst for ammonia synthesis. However, compared to Fe, N<sub>2</sub> has higher activation energy barrier for the dissociation process (0.4 eV) and the subsequent subsurface diffusion process (1.4 eV). As a result, the authors of that study concluded that nitrogen transport through a pure V membrane may be difficult to achieve. V-Ru alloys, on the other hand, may have the potential to be used as membrane materials, *i.e.*, DFT simulations performed in that study showed that the presence of Ru weakens the adsorption of nitrogen in the first subsurface layer, which enhances the diffusion of atomic nitrogen. Wang *et al.*[129] revealed that the graphene membrane with nanopores formed by replacing 13 C atoms with H atoms (H-pore-13) can efficiently separate N<sub>2</sub> from CO<sub>2</sub> despite the

fact that the size of the pore (4.06 Å) is larger than the size of both N<sub>2</sub> and CO<sub>2</sub> molecules. The authors further studied this phenomenon using dispersion-corrected DFT by portraying the potential energy profiles of N<sub>2</sub> and CO<sub>2</sub> molecules penetrating through the pore. The profile showed that CO<sub>2</sub> and N<sub>2</sub> molecules interact with the pore most strongly at 2.0 Å and 1.6 Å above the surface with interaction energies of 0.24 eV and 0.14 eV, respectively. Moreover, the energy barriers to pass through the pore are 0.19 eV for CO<sub>2</sub> molecule and 0.05 eV for N<sub>2</sub> molecule. Hence, it is more difficult for CO<sub>2</sub> to permeate the membrane compared with N<sub>2</sub>. Similar methods were also used to examine the N<sub>2</sub> selectivity of the poly-(triazine imide) (PTI) membrane[130]. The computed energy barriers for CO<sub>2</sub>, N<sub>2</sub> and H<sub>2</sub>O passing through the PTI membrane are 0.262, 0.118, and 0.164 eV respectively, which suggests that PTI is also a promising material for N<sub>2</sub>/CO<sub>2</sub> separating membranes.

DFT analysis has been successfully employed to theoretically investigate and predict the applicability of a wide range of materials in membrane technology. More studies are expected in this field in order to provide guidance to the experimental work and allow experimental scientists to make decisions faster thus enabling the rapid development of new and optimized membrane materials for CO<sub>2</sub> capture technologies.

## 2.4 Zeolites

Zeolites are crystallized porous aluminosilicates that contain exchangeable cations (Li<sup>+</sup>, Na<sup>+</sup>, Ca<sup>2+</sup>, etc.). Due to the cages and channels as well as the changeable cations, zeolites have been widely used in pre-combustion and post-combustion CO<sub>2</sub> capture applications. The diversity of zeolites makes these materials attractive for the CO<sub>2</sub> adsorption process. For example, the topologies, the number of exchangeable cations in the cavities, pore sizes and Si/Al ratio are important criteria that needs to be considered in the selection of zeolites for CO<sub>2</sub> adsorption[131],[132].

DFT analysis of zeolites as CO<sub>2</sub> adsorbents can predict the adsorption behavior such as adsorption capacity, favored sites and selective adsorption among gaseous mixtures. Zukal *et al.*[31] reported the CO<sub>2</sub> adsorption in Na-A zeolites using a periodic slab model to provide accurate predictions of the dispersion interactions. That study showed that simulation results agree well with the experimental outcomes and CO<sub>2</sub> tends to be stable when it interacts with 3 Na<sup>+</sup> cations simultaneously. Thang *et al.*[133] studied the faujasite-type zeolites using the DFT/CC (coupled cluster)

method[134]. Compared to results reported from other simulation methods, a better prediction of the interaction energy through DFT/CC calculations was obtained in that study, which has also been shown to agree well with experimental results. Cation site effects have been studied by Nachtigall *et al.*[32]. In that study, periodic DFT calculations indicate that dual or multiple cation sites tend to adsorb gas molecules rather than single cation sites. As for CO<sub>2</sub> in mixtures, the selective adsorption of CO<sub>2</sub> over N<sub>2</sub> (exhaust gas composition) is studied with a NaKA zeolite (Na-A type zeolite with partial substitution of Na<sup>+</sup> by K<sup>+</sup>)[46]. Both the isolated cluster and the periodic model were adopted in that study and have shown that it is the high carbonate forming at the K<sup>+</sup> ion positions in the 8R windows, which enhances the selectivity towards CO<sub>2</sub> adsorption. Another focus of selective adsorption on CO<sub>2</sub> is with natural gas (i.e. a mixture of CO<sub>2</sub> and CH<sub>4</sub>). Fischer *et al.*[135] conducted the dispersion-corrected DFT calculations to estimate the interactions of the adsorbed molecules (CO<sub>2</sub>, N<sub>2</sub> and CH<sub>4</sub>) with different synthetic zeolites. The results from that work showed that the difference in the binding energy between zeolite-CO<sub>2</sub> and zeolite-CH<sub>4</sub> in K<sup>+</sup> or Rb<sup>+</sup> containing adsorbents is significant for the selective adsorption of CO<sub>2</sub>. Compared to other CO<sub>2</sub> capture materials such as MOFs, DFT studies using zeolites are limited despite the fact that atomistic computational methods have shown to be efficient to predict CO<sub>2</sub> adsorption phenomena.

## 2.5 Ionic liquids

Ionic liquids (ILs) are considered promising candidates in industrial processes for conventional volatile compounds separation and storage[136]. ILs are salts with melting points lower than 100 °C[137]. This type of materials often present excellent thermal stability, good solubility as well as the possibility of ionic and composition substitutions, which make them attractive for different industrial applications including CO<sub>2</sub> capture. ILs also allow the combination of different ions, which offers the flexibility to tune materials for further improvement. This makes ILs particularly attractive since they offer the potential to be designed for specific purposes. Compared with experimental reports, DFT analysis is an efficient and inexpensive approach that can be employed to screen a large number of potential ILs to build up specific structure-property relationships. ILs are popular in the area of CO<sub>2</sub> capture due to its experimentally reported high CO<sub>2</sub> capture capacities and its desirable chemical or physical properties[34],[138],[139].

DFT analysis on ILs applied for CO<sub>2</sub> capture is usually combined with molecular dynamic simulations (MD). DFT simulations predict the charge distribution and charge transfer, structural and energetic properties of short-range intermolecular interactions within isolated ions, ion-ion and ion-CO<sub>2</sub> mixtures[140]. On the other hand, MD predicts the dynamic properties of the systems such as the diffusivity of CO<sub>2</sub> confined at specific pressures and temperatures. Aparicio *et al.*[141] reported the microscopic structures and intermolecular forces of choline benzoate and choline salicylate ILs in the pure state and also in the CO<sub>2</sub> absorption process. The studied CO<sub>2</sub>-ion pairs show strong interactions with benzoate anion. The volume increase of the studied ions, cholinium benzoate ([BE][CH]) and cholinium salicylate ([SA][CH]), is apparently larger than other ions such as lactate[142]. The mechanism of CO<sub>2</sub> absorption on the studied ILs as well as the CO<sub>2</sub> effects are provided. That study reported that there is no overlap in the system containing the studied ions and CO<sub>2</sub>. Also, the CO<sub>2</sub> absorption increases the molecular mobility and viscosity of the heterogeneous systems. Shaikh *et al.*[33] used DFT analysis and MD simulations to predict CO<sub>2</sub> absorption on amino acid ionic liquids (AAILs). That study showed that glycinate ([GLY]) adsorbs CO<sub>2</sub> better than 1,1,1-trimethylhydrazinium ([aN111]) though [GLY] increased the liquid viscosity. The balance of high CO<sub>2</sub> capture capacity and low viscosity should therefore be taken into account for AAILs. Steckel[137] studied the interaction of CO<sub>2</sub> with acetate ion. Multiple DFT functionals were evaluated and have shown that they were not able to accurately reproduce all the geometries and energetic calculations obtained from coupled-cluster singles and doubles (CCSD) optimizations; on the other hand, the range-separated hybrid meta-GGA[143] (M11) and nonlocal (VV10[144] and vdWDF10[145]) functionals lead to better results among all the studied DFT methods. That study gives guidance of DFT-based MD calculations and the parametrization of the force fields based on DFT analysis. Damas *et al.*[146] used DFT to evaluate the interactions of cations and anions derived from ionic liquids with CO<sub>2</sub>, SO<sub>2</sub> and H<sub>2</sub>S. The results suggest that IL-based anions are more likely to interact with CO<sub>2</sub> when the cation-anion interactions are weaker. That study provides a comprehensive mechanism of the studied system and more absorption species since it extends on a previous report[147] that only considered CO<sub>2</sub> capture adopting the 1-ethyl-3-methylimidazolium (C<sub>2</sub>mim<sup>+</sup>) and bis(trifluorosulfonyl)imide (Tf<sub>2</sub>N). Garcia *et al.*[148] screened different density functional methods to study CO<sub>2</sub> capture by ILs. Binding energies of gas-ILs of a set of 54 ILs were estimated. The results show that

$\omega$ B97XD[149] can simulate the long-range corrections to provide suitable charge transfer considering the dispersion corrections through DFT-D2 approach[150]. The resulting correlations between CO<sub>2</sub> and ILs are key to optimize the design of ILs for CO<sub>2</sub> capture. To mimick the interactions in consideration of both physical and chemical absorption, a new force field was developed in CO<sub>2</sub> absorption on ILs. Zhang *et al.*[35] developed a ReaxFF force field based on CO<sub>2</sub> capture by tetrabutylphosphonium glycinate, [P(C<sub>4</sub>)<sub>4</sub>][Gly]. The resulting force field is used in NPT ensemble MD simulations to predict the equilibrium density at 300K and 1 atm. Multiple sets of interactions are considered such as periodic DFT simulations of the reaction pathways between CO<sub>2</sub> and anion in the condensed phase, gas-phase CO<sub>2</sub>-anion interactions. The ReaxFF-based MD simulation predicts the equilibrium density at 300 K, which is within about 1% of the experimental value. Mondal *et al.*[151] provided force field parameters for imidazolium cation based ILs combining anions of acetate, thiocyanate and dicyanamide. The DFT derived fractional charges were used to modify the CLaP force field[152],[153],[154] and build a transferable force field. The improved force field was used in MD simulations and showed that the intermolecular structure and dynamics agree well with experimental results. That work showed that the scheme used to define the non-bonded and torsional interaction parameters by the partial charges can be used to establish transferable force fields in this area.

The DFT studies of ILs discussed above show that simulations are powerful tools to screen this highly diverse and tunable material based on the specific targets pursued for CO<sub>2</sub> absorption. However, some aspects of greenhouse emission disposal are still under debate using ILs. Further research on absorption selectivity of CO<sub>2</sub> over impurities is therefore needed to further support the development of this material for CO<sub>2</sub> capture applications.

## 2.6 Additional materials

The materials discussed in the previous sections represent the most commonly used materials considered for CO<sub>2</sub> capture. First principles (DFT) studies on other materials that have shown potential as attractive CO<sub>2</sub> adsorbents. These materials are discussed next.

Porous carbons stand out in the area of CO<sub>2</sub> adsorption due to their relatively low prices compared to the other materials such as MOFs[16]. In addition, a variety of

allotropes of carbon such as nanotubes or graphenes allow the specific applications of porous carbons. Mo *et al.*[37] conducted a functionalized carbon study to analyze CO<sub>2</sub> adsorption. The N-containing molecular segment models of coal (2-methylpyridine, C<sub>13</sub>H<sub>9</sub>N, C<sub>23</sub>H<sub>12</sub>N, and N-doped graphenes) was evaluated by CO<sub>2</sub> uptakes. That study found that the DFT method of BLYP-D3 combined with a 6-311++G (d, p) basis set can accurately simulate the interactions in the studied particles such as 2-methylpyridine, C<sub>13</sub>H<sub>9</sub>N and C<sub>23</sub>H<sub>12</sub>N, which improves the accuracy of the calculations of CO<sub>2</sub> adsorption in the system containing similar compositions. Jiao *et al.*[36] showed that the addition of pyridinic-nitrogen in nanotubes enhances CO<sub>2</sub> adsorption strength with varying charge states. That study showed that reversible CO<sub>2</sub> adsorption (i.e. desorption) can be controlled through the injection of electrons into the nanotubes. Then, the idea of switching the charge-carrying states of the nanotubes becomes a new scheme for CO<sub>2</sub> uptakes. As for fullerene (C<sub>60</sub>), Gao *et al.*[155] used DFT analysis to evaluate the potential application of fullerene of CO<sub>2</sub> adsorption. Their results showed that calcium decorated fullerene have the potential to adsorb 16 CO<sub>2</sub> molecules in a unit cluster with 4 decorated Ca atoms. Graphene has also been studied for CO<sub>2</sub> adsorption using DFT calculations. Rad *et al.*[38] provided microscopic information of the CO<sub>2</sub> uptakes by Al-doped graphene such as the adsorption energy and electronic states. The outcomes of that study showed the potential of functionalized graphene materials as CO<sub>2</sub> adsorbents. Another porous carbon materials that have been studied are mesoporous silica nanoparticles such as SBA-15[39] or MCM-41[40]. Zhuo *et al.*[156] simulated the CO<sub>2</sub> and N<sub>2</sub> adsorption on mimetic MCM-41. DFT analysis of this system showed that CO<sub>2</sub> has preferable adsorption sites over N<sub>2</sub> on the materials' surface. MCM-41 also has higher adsorption selectivity of CO<sub>2</sub> over N<sub>2</sub>. As for SBA-15, Zupal *et al.*[157] evaluated the functionalized SBA-15 with 3-aminopropyl-trimethoxysilane using the CO<sub>2</sub> adsorption energy distribution obtained from non-local DFT calculations. That study revealed that amine ligands on the surface seem to enhance CO<sub>2</sub> capture on the studied material. The CO<sub>2</sub> adsorption capacity of the studied material is highly related to the amount of amine groups. Especially, the tethered amine ligands react strongly with CO<sub>2</sub> to form a carbamate. The high isosteric heats of adsorption indicate that strong interactions between CO<sub>2</sub> and amine groups exist. Amine-based solvents, e.g. monoethanolamine (MEA), appears to be the most promising and widely used materials in amine scrubbing post-combustion technology to capture CO<sub>2</sub>[42],[43],[158],[159],[160],[161],[162]. Yamada *et al.*[48] developed a continuum

solvation model (SMD)[47] in DFT analysis to study the CO<sub>2</sub> absorption in an aqueous solution of 2-amino-2methyl-1-propanol (AMP). SMD is popular to predict solvation free energies of neutral and ionic in the solutions. The established pathway of CO<sub>2</sub> absorption is a two step mechanism via a zwitterion intermediate. The carbamate forms fast and decomposes reversibly. Except for the materials mentioned in this section, an increasing number of innovative materials are considered in the area of CO<sub>2</sub> capture, such as new polymers[163], zinc orthogermanate[164], perovskite[165], metal oxides[166][167] and hydrotalcite[168]. Polymers have attracted much attention recently due to their structural tunability[163]. In particular, Zinc orthogermanate (Zn<sub>2</sub>GeO<sub>4</sub>) is a polymer ternary oxide material that has shown to be promising to capture CO<sub>2</sub> in photoreduction. This material plays a vital role to improve the reduction of CO<sub>2</sub> into renewable hydrocarbon fuel as a photocatalyst[164]. In addition, perovskites can be regarded as composite OCs that have high activities and also favour ionic and electronic migration during the redox reactions [169]. Unlike other OC materials, perovskites allow relatively low energy for oxygen anions and electron transport from the bulk to the active surface. The urgent need for high efficient CO<sub>2</sub> disposal technologies encourages practitioners to explore new and novel materials with suitable properties for CO<sub>2</sub> capture.

### 3. Summary

This review has presented the recent contributions and advances on first-principles (DFT) modelling applied to the design of materials suitable for CO<sub>2</sub> capture technologies. Testing and validation of computer aided design materials using experiments will shed light into the development of new materials that can eventually promote the sustainable production of power using fossil-fired systems. The oxygen carrier (OC) used in CLC has attracted much attention due to its energy efficiency since it makes use of oxy-combustion process through a 2-reactor scheme. The application of OCs in different systems still requires more research in DFT analysis to provide microscopic structure-property relations, which will guide the design of materials depending on the specific CO<sub>2</sub> capture targets. MOFs and ILs are both favored by their tunable properties since in principle they can be designed to satisfy a specific separation target requirement. The focus of MOFs in the application of CO<sub>2</sub> capture is on its unsaturated sites as well as the breathing property of some of the specific MOFs. On the other hand, zeolites, porous carbons, amine-based solutions are relatively mature candidates in the area of CO<sub>2</sub> disposal, which are currently

applied in industry. However, insights on the mechanisms and microscopic structures of the systems using these relatively traditional materials are still lacking in the literature. DFT methods can significantly enhance the application of these materials since they can reveal properties that can be exploited for CO<sub>2</sub> capture. Computational modelling allows efficient screening of a large set of materials and can accelerate the development of novel materials that can support fossil-fired power production under near zero emissions. Therefore, modelling studies in this area can drive the design and optimization of new materials with properties ideally suited for CO<sub>2</sub> capture thus promoting the sustainability of new and efficient CO<sub>2</sub> capture technologies.

## Acknowledgements

The authors gratefully acknowledge the support provided by the Chinese Scholarship Council to develop this research.

## References

- [1] H.C.J. Godfray, J.R. Beddington, I.R. Crute, L. Haddad, D. Lawrence, J.F. Muir, J. Pretty, S. Robinson, S.M. Thomas, C. Toulmin, Food Security: The Challenge of Feeding 9 Billion People. *Science*. (2010) 1185383.
- [2] F. Tonelli, S. Evans, P. Taticchi, Industrial sustainability: challenges, perspectives, actions. *IJBI*. 7 (2013) 143.
- [3] E.W.T. Ngai, C.T. Daniel Ng, G.Q. Huang, Energy sustainability for production design and operations. *Int. J. Prod. Econ.* 146 (2) (2013) 383-385.
- [4] P.V. Kamat, Meeting the clean energy demand: nanostructure architectures for solar energy conversion. *J. Phys. Chem. C*. 111 (7) (2007) 2834-2860.
- [5] A. Betancourt-Torcat, A. Elkamel, L. Ricardez-Sandoval, Optimal integration of nuclear energy and water management into the oil sands operations. *Aiche J.* 58 (11) (2012) 3433-3453.
- [6] S. Suthar, A.K. Nema, M. Chabukdhara, S.K. Gupta, Assessment of metals in water and sediments of Hindon River, India: impact of industrial and urban discharges. *J Hazard Mater.* 171 (1-3) (2009) 1088-95.
- [7] M. Moradi-Aliabadi, Y. Huang, Decision Support for Enhancement of Manufacturing Sustainability: A Hierarchical Control Approach. *ACS Sustainable Chem. Eng.* 6 (4) (2018) 4809-4820.
- [8] M. Moradi-Aliabadi, Y. Huang, Multistage Optimization for Chemical Process Sustainability Enhancement under Uncertainty. *ACS Sustainable Chem. Eng.* 4 (11) (2016) 6133-6143.
- [9] J. Adanez, A. Abad, F. Garcia-Labiano, P. Gayan, L.F. de Diego, Progress in Chemical-Looping Combustion and Reforming technologies. *Prog. Energy Combust. Sci.* 38 (2) (2012) 215-282.
- [10] S.C. Bayham, A. Tong, M. Kathe, L.-S. Fan, Chemical looping technology for energy and chemical production. *Wires. Energy Environ.* 5 (2) (2016) 216-241.
- [11] F. Birol, *Key world energy statistics*, (2017).

- [12] M. Hossein Sahraei, D. McCalden, R. Hughes, L.A. Ricardez-Sandoval, A survey on current advanced IGCC power plant technologies, sensors and control systems. *Fuel*. 137 (2014) 245-259.
- [13] S. Mills, Coal-fired CCS demonstration plants, 2012. *IEA Clean Coal Centre: London, UK*. (2012).
- [14] L.F. de Diego, F. García-Labiano, P. Gayán, J. Celaya, J.M. Palacios, J. Adánez, Operation of A 10 kWth Chemical-looping Combustor during 200 h with A CuO-Al<sub>2</sub>O<sub>3</sub> Oxygen Carrier. *Fuel*. 86 (2007) 1036-1045.
- [15] A. Nandy, C. Loha, S. Gu, P. Sarkar, M.K. Karmakar, P.K. Chatterjee, Present status and overview of Chemical Looping Combustion technology. *Renew. Sust. Energ. Rev.* 59 (2016) 597-619.
- [16] D.M. D'Alessandro, B. Smit, J.R. Long, Carbon dioxide capture: prospects for new materials. *Angew Chem Int Ed Engl.* 49 (35) (2010) 6058-82.
- [17] J.D. Figueroa, T. Fout, S. Plasynski, H. McIlvried, R.D. Srivastava, Advances in CO<sub>2</sub> capture technology-The U.S. Department of Energy's Carbon Sequestration Program. *Int. J. Greenh. Gas Con.* 2 (2008) 9-20.
- [18] S. Vasudevan, S. Farooq, I.A. Karimi, M. Saeys, M.C.G. Quah, R. Agrawal, Energy penalty estimates for CO<sub>2</sub> capture: Comparison between fuel types and capture-combustion modes. *Energy*. 103 (2016) 709-714.
- [19] B. Metz, *Carbon dioxide capture and storage: special report of the intergovernmental panel on climate change*. Cambridge University Press: 2005.
- [20] T. Nittaya, P.L. Douglas, E. Croiset, L.A. Ricardez-Sandoval, Dynamic Modelling and Controllability Studies of a Commercial-scale MEA Absorption Processes for CO<sub>2</sub> Capture from Coal-fired Power Plants. *Energy Procedia*. 63 (2014) 1595-1600.
- [21] M. Hossein Sahraei, L.A. Ricardez-Sandoval, Controllability and optimal scheduling of a CO<sub>2</sub> capture plant using model predictive control. *Int. J. Greenh. Gas Con.* 30 (2014) 58-71.
- [22] C. Dong, S. Sheng, W. Qin, Q. Lu, Y. Zhao, X. Wang, J. Zhang, Density functional theory study on activity of alpha-Fe<sub>2</sub>O<sub>3</sub> in chemical-looping combustion system. *Appl. Surf. Sci.* 257 (2011) 8647-8652.
- [23] X. Cai, X. Wang, X. Guo, C.g. Zheng, Mechanism study of reaction between CO and NiO(001) surface during chemical-looping combustion: Role of oxygen. *Chem. Eng. J.* 244 (2014) 464-472.
- [24] F. Li, S. Luo, Z. Sun, X. Bao, L.-S. Fan, Role of metal oxide support in redox reactions of iron oxide for chemical looping applications: experiments and density functional theory calculations. *Energy Environ. Sci.* 4 (2011) 3661-3667.
- [25] L. Zhao, Q.Y. Yang, Q.T. Ma, C.L. Zhong, J.G. Mi, D.H. Liu, A force field for dynamic Cu-BTC metal-organic framework. *J. Mol. Model.* 17 (2) (2011) 227-234.
- [26] M.A. Hussain, Y. Soujanya, G.N. Sastry, Computational Design of Functionalized Imidazolate Linkers of Zeolitic Imidazolate Frameworks for Enhanced CO<sub>2</sub> Adsorption. *J. Phys. Chem. C*. 119 (41) (2015) 23607-23618.
- [27] D.D. Borges, M. Prakash, N.A. Ramsahye, P.L. Llewellyn, S. Surble, P. Horcajada, C. Serre, G. Maurin, Computational exploration of the gas adsorption on the iron tetracarboxylate metal-organic framework MIL-102. *Mol. Simulat.* 41 (16-17) (2015) 1357-1370.
- [28] S.N. Paglieri, J.D. Way, Innovations in palladium membrane research. *Sep. Purif. Methods*. 31 (1) (2002) 1-169.
- [29] Y. Wang, W. Wang, S. Zhu, L. Guo, Z. Zhang, P. Li, The mechanisms study of the porous graphene for the purification of the mixed gases: A multi-scale computational method. *Comp. Mater. Sci.* 143

(2018) 277-285.

- [30] T. Watanabe, S. Keskin, S. Nair, D.S. Sholl, Computational identification of a metal organic framework for high selectivity membrane-based CO<sub>2</sub>/CH<sub>4</sub> separations: Cu(hfipbb)(H<sub>2</sub>hfipbb)<sub>0.5</sub>. *Phys. Chem. Chem. Phys.* **11** (48) (2009) 11389-11394.
- [31] A. Zukal, C.O. Arean, M.R. Delgado, P. Nachtigall, A. Pulido, J. Mayerová, J. Čejka, Combined volumetric, infrared spectroscopic and theoretical investigation of CO<sub>2</sub> adsorption on Na-A zeolite. *Microporous Mesoporous Mater.* **146** (1-3) (2011) 97-105.
- [32] P. Nachtigall, M.R. Delgado, D. Nachtigallova, C.O. Arean, The nature of cationic adsorption sites in alkaline zeolites--single, dual and multiple cation sites. *Phys Chem Chem Phys.* **14** (5) (2012) 1552-69.
- [33] A.R. Shaikh, H. Karkhanechi, E. Kamio, T. Yoshioka, H. Matsuyama, Quantum Mechanical and Molecular Dynamics Simulations of Dual-Amino-Acid Ionic Liquids for CO<sub>2</sub> Capture. *J. Phys. Chem. C.* **120** (49) (2016) 27734-27745.
- [34] G. Garcia, M. Atilhan, S. Aparicio, Simultaneous CO<sub>2</sub> and SO<sub>2</sub> capture by using ionic liquids: a theoretical approach. *Phys. Chem. Chem. Phys.* **19** (7) (2017) 5411-5422.
- [35] B. Zhang, A.C.T. van Duin, J.K. Johnson, Development of a ReaxFF Reactive Force Field for Tetrabutylphosphonium Glycinate/CO<sub>2</sub> Mixtures. *J. Phys. Chem. B.* **118** (41) (2014) 12008-12016.
- [36] Y. Jiao, Y. Zheng, S.C. Smith, A.J. Du, Z.H. Zhu, Electrocatalytically Switchable CO<sub>2</sub> Capture: First Principle Computational Exploration of Carbon Nanotubes with Pyridinic Nitrogen. *Chemsuschem.* **7** (2) (2014) 435-441.
- [37] J.J. Mo, Y. Xue, X.Q. Liu, N.X. Qiu, W. Chu, H.P. Xie, Quantum chemical studies on adsorption of CO<sub>2</sub> on nitrogen-containing molecular segment models of coal. *Surf. Sci.* **616** (2013) 85-92.
- [38] A.S. Rad, V.P. Foukoliaei, Density functional study of Al-doped graphene nanostructure towards adsorption of CO, CO<sub>2</sub> and H<sub>2</sub>O. *Synth. Met.* **210** (2015) 171-178.
- [39] M. Kruk, M. Jaroniec, C.H. Ko, R. Ryoo, Characterization of the porous structure of SBA-15. *Chem. Mater.* **12** (7) (2000) 1961-1968.
- [40] A. Cauvel, D. Brunel, F. DiRenzo, F. Fajula, Organic lining of MCM-41-type silicas, AIP Conference Proceedings, Woodbury, 1996.
- [41] T.T. Zhang, Y.S. Yu, Z.X. Zhang, An interactive chemical enhancement of CO<sub>2</sub> capture in the MEA/PZ/AMP/DEA binary solutions. *Int. J. Greenh. Gas Con.* **74** (2018) 119-129.
- [42] H.M. Stowe, G.S. Hwang, Fundamental Understanding of CO<sub>2</sub> Capture and Regeneration in Aqueous Amines from First-Principles Studies: Recent Progress and Remaining Challenges. *Ind. Eng. Chem. Res.* **56** (24) (2017) 6887-6899.
- [43] T. Nittaya, P.L. Douglas, E. Croiset, L.A. Ricardez-Sandoval, Dynamic Modeling and Evaluation of an Industrial-Scale CO<sub>2</sub> Capture Plant Using Monoethanolamine Absorption Processes. *Ind. Eng. Chem. Res.* **53** (28) (2014) 11411-11426.
- [44] J.-C. Charpentier, In the frame of globalization and sustainability, process intensification, a path to the future of chemical and process engineering (molecules into money). *Chem. Eng. J.* **134** (1-3) (2007) 84-92.
- [45] D. Sholl, J.A. Steckel, *Density functional theory: a practical introduction*. John Wiley & Sons: 2011.
- [46] A.V. Larin, A. Mace, A.A. Rybakov, A. Laaksonen, Carbonate "door" in the NaKA zeolite as the reason of higher CO<sub>2</sub> uptake relative to N<sub>2</sub>. *Microporous Mesoporous Mater.* **162** (2012) 98-104.
- [47] A.V. Marenich, C.J. Cramer, D.G. Truhlar, Universal solvation model based on solute electron

density and on a continuum model of the solvent defined by the bulk dielectric constant and atomic surface tensions. *J. Phys. Chem. B.* 113 (18) (2009) 6378-6396.

[48] H. Yamada, Y. Matsuzaki, T. Higashii, S. Kazama, Density Functional Theory Study on Carbon Dioxide Absorption into Aqueous Solutions of 2-Amino-2-methyl-1-propanol Using a Continuum Solvation Model. *J. Phys. Chem. A.* 115 (14) (2011) 3079-3086.

[49] K. Reuter, M. Scheffler, Composition, structure, and stability of RuO<sub>2</sub>(110) as a function of oxygen pressure. *Phys. Rev. B.* 65 (3) (2001).

[50] K. Reuter, M. Scheffler, Composition and structure of the RuO<sub>2</sub>(110) surface in an O<sub>2</sub> and CO environment: Implications for the catalytic formation of CO<sub>2</sub>. *Phys. Rev. B.* 68 (4) (2003).

[51] H. Yang, Z. Xu, M. Fan, R.B. Slimane, A.E. Bland, I. Wright, Progress in carbon dioxide separation and capture: A review. *J. Environ. Sci.* 20 (2008) 14-27.

[52] A. Lyngfelt, B. Leckner, T. Mattisson, A fluidized-bed combustion process with inherent CO<sub>2</sub> separation; application of chemical-looping combustion. *Chem. Eng. Sci.* 56 (10) (2001) 3101-3113.

[53] H. Leion, T. Mattisson, A. Lyngfelt, Solid fuels in chemical-looping combustion. *Int. J. Greenh. Gas Con.* 2 (2) (2008) 180-193.

[54] E. Jerndal, T. Mattisson, A. Lyngfelt, Thermal analysis of chemical-looping combustion. *Chem. Eng. Res. Des.* 84 (A9) (2006) 795-806.

[55] P. Cho, T. Mattisson, A. Lyngfelt, Comparison of iron-, nickel-, copper- and manganese-based oxygen carriers for chemical-looping combustion. *Fuel.* 83 (9) (2004) 1215-1225.

[56] Y. Li, C. Zhao, H. Chen, Y. Liu, Enhancement of Ca-Based Sorbent Multicyclic Behavior in Ca Looping Process for CO<sub>2</sub> Separation. *Chem. Eng. Technol.* 32 (4) (2009) 548-555.

[57] I. Martínez, B. Arias, G.S. Grasa, J.C. Abanades, CO<sub>2</sub> capture in existing power plants using second generation Ca-Looping systems firing biomass in the calciner. *Journal of Cleaner Production.* 187 (2018) 638-649.

[58] L. Liu, D. Hong, X. Guo, A study of metals promoted CaO-based CO<sub>2</sub> sorbents for high temperature application by combining experimental and DFT calculations. *Journal of CO<sub>2</sub> Utilization.* 22 (2017) 155-163.

[59] M. Schmitz, C.J. Linderholm, Performance of calcium manganate as oxygen carrier in chemical looping combustion of biochar in a 10kW pilot. *Appl. Energ.* 169 (2016) 729-737.

[60] M. Mehrpooya, M.M. Moftakhari Sharifzadeh, M. Rajabi, M. Aghbashlo, M. Tabatabai, S. Hosseinpour, S. Ramakrishna, Design of an integrated process for simultaneous chemical looping hydrogen production and electricity generation with CO<sub>2</sub> capture. *Int. J. Hydrogen Energy.* 42 (12) (2017) 8486-8496.

[61] H. Fang, L. Haibin, Z. Zengli, Advancements in development of chemical-looping combustion: A review. *Int. J. Chem. Eng.* 2009 (2009) 1-16.

[62] P. Verma, A. Perera, R.J. Bartlett, Increasing the applicability of DFT I: Non-variational correlation corrections from Hartree-Fock DFT for predicting transition states. *Chem. Phys. Lett.* 524 (2012) 10-15.

[63] N. Latelli, N. Ouddai, M. Arotcarena, P. Chaumont, P. Mignon, H. Chermette, Mechanism of addition-fragmentation reaction of thiocarbonyl compounds in free radical polymerization. A DFT study. *Comput. Theor. Chem.* 1027 (2014) 39-45.

[64] J.D. Chai, Role of exact exchange in thermally-assisted-occupation density functional theory: A proposal of new hybrid schemes. *J. Chem. Phys.* 146 (4) (2017).

[65] E.F.V. Carvalho, A.N. Barauna, F.B.C. Machado, O. Roberto-Neto, DFT study for the reactions of

- H atoms with CH<sub>3</sub>OH and C<sub>2</sub>H<sub>5</sub>OH. *Int. J. Quantum Chem.* 108 (13) (2008) 2476-2485.
- [66] Q. Tan, W. Qin, Q. Chen, C. Dong, W. Li, Y. Yang, Synergetic Effect of ZrO<sub>2</sub> on The Oxidation-reduction Reaction of Fe<sub>2</sub>O<sub>3</sub> during Chemical Looping Combustion. *Appl. Surf. Sci.* 258 (2012) 10022-10027.
- [67] Z. Cheng, L. Qin, M. Guo, M. Xu, J.A. Fan, L.-S. Fan, Oxygen vacancy promoted methane partial oxidation over iron oxide oxygen carriers in the chemical looping process. *Phys. Chem. Chem. Phys.* 18 (2016) 32418-32428.
- [68] Y. Zhang, H. Zhao, L. Guo, C. Zheng, Decomposition Mechanisms of Cu-based Oxygen Carriers for Chemical Looping with Oxygen Uncoupling Based on Density Functional Theory Calculations. *Combust. Flame.* 162 (2015) 1265-1274.
- [69] Y. Feng, X. Guo, Study of reaction mechanism of methane conversion over Ni-based oxygen carrier in chemical looping reforming. *Fuel.* 210 (2017) 866-872.
- [70] H. You, Y. Yuan, J. Li, L. Ricardez-Sandoval, A Multi-scale model for CO<sub>2</sub> capture: A Nickel-based oxygen carrier in Chemical-looping Combustion, 10th IFAC Symposium on Advanced Control of Chemical Processes, Shenyang, China, 2018.
- [71] W. Qin, C.F. Lin, D.T. Long, X.B. Xiao, C.Q. Dong, Reaction Activity and Deep Reduction Reaction Mechanism of a High Index Iron Oxide Surface in Chemical Looping Combustion. *Acta Physico-Chimica Sinica.* 31 (2015) 667-675.
- [72] C. Lin, W. Qin, C. Dong, Reduction effect of  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> on carbon deposition and CO oxidation during chemical-looping combustion. *Chem. Eng. J.* 301 (2016) 257-265.
- [73] J. Zhang, W. Qin, C. Dong, Y. Yang, Density Functional Theory Study of Elemental Mercury Adsorption on Fe<sub>2</sub>O<sub>3</sub>[104] and Its Effect on Carbon Deposit during Chemical Looping Combustion. *Energ. Fuel.* 30 (2016) 3413-3418.
- [74] L. Wang, L. Wu, C. Dong, J. Zhang, W. Qin, Theoretical study on reactivity of Fe-based oxygen carrier with CH<sub>4</sub> during chemical looping combustion. *Appl. Mech. Mater.* 345 (2013) 298-301.
- [75] L. Huang, M. Tang, M. Fan, H. Cheng, Density functional theory study on the reaction between hematite and methane during chemical looping process. *Appl. Energ.* 159 (2015) 132-144.
- [76] J.J. Tang, B. Liu, Reactivity of the Fe<sub>2</sub>O<sub>3</sub>(0001) Surface for Methane Oxidation: A GGA + U Study. *J. Phys. Chem. C.* 120 (2016) 6642-6650.
- [77] D. Chang Qing, Z. Xiao Lei, Y. Yong Ping, Density Functional Study of the C Atom Adsorption on the  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> (001) Surface. *Chinese J. Struct. Chem.* 30 (2011) 17-24.
- [78] W. Qin, C.F. Lin, D.T. Long, J.Y. Wang, C.Q. Dong, Activity of Fe<sub>2</sub>O<sub>3</sub> with a high index facet for bituminous coal chemical looping combustion: a theoretical and experimental study. *RSC Adv.* 6 (2016) 85551-85558.
- [79] C. Dong, X. Liu, W. Qin, Q. Lu, X. Wang, S. Shi, Y. Yang, Deep reduction behavior of iron oxide and its effect on direct CO oxidation. *Appl. Surf. Sci.* 258 (2012) 2562-2569.
- [80] W. Qin, Q. Chen, Y. Wang, C. Dong, J. Zhang, W. Li, Y. Yang, Theoretical Study of Oxidation-reduction Reaction of Fe<sub>2</sub>O<sub>3</sub> Supported on MgO during Chemical Looping Combustion. *Appl. Surf. Sci.* 266 (2013) 350-354.
- [81] H. Zhao, Y. Zhang, Y. Wei, J. Gui, Understanding CuO-support interaction in Cu-based oxygen carriers at a microcosmic level. *Proceedings of the Combustion Institute.* 36 (2017) 4069-4077.
- [82] Z. Xu, H. Zhao, Y. Wei, C. Zheng, Self-assembly template combustion synthesis of a core-shell CuO@TiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> hierarchical structure as an oxygen carrier for the chemical-looping processes. *Combust. Flame.* 162 (2015) 3030-3045.

- [83] W. Li, Q. Chen, W. Qin, N. Wang, J. Lai, Interaction of CO with CuO and CuO/graphene: Reactions mechanism and the Formation of CO<sub>2</sub>. *Adv. Mat. Res.* 354 (2012) 279-285.
- [84] M. Wang, J. Liu, F. Shen, H. Cheng, J. Dai, Y. Long, Theoretical Study of Stability and Reaction Mechanism of CuO Supported on ZrO<sub>2</sub> during Chemical Looping Combustion. *Appl. Surf. Sci.* 367 (2016) 485-492.
- [85] M. Wang, J. Liu, J. Hu, F. Liu, O<sub>2</sub>-CO<sub>2</sub> Mixed Gas Production Using a Zr-Doped Cu-Based Oxygen Carrier. *Industrial and Engineering Chemistry Research.* 54 (2015) 9805-9812.
- [86] Y. Feng, X. Cai, X. Guo, C. Zheng, Influence mechanism of H<sub>2</sub>S on the reactivity of Ni-based oxygen carriers for chemical-looping combustion. *Chem. Eng. J.* 295 (2016) 461-467.
- [87] L. Qin, Z. Cheng, M. Guo, J.a. Fan, L.S. Fan, Morphology evolution and nanostructure of chemical looping transition metal oxide materials upon redox processes. *Acta Mater.* 124 (2017) 568-578.
- [88] W.Y. Li, Q.L. Chen, Density Functional Theory Study of Oxygen Carrier Mn<sub>3</sub>O<sub>4</sub>(001) surface Reaction with CO. *Adv. Mat. Res.* 479 (2012) 81-87.
- [89] X. Zhang, X. Song, Z. Sun, P. Li, J. Yu, Density functional theory study on the mechanism of calcium sulfate reductive decomposition by methane. *Fuel.* 110 (2013) 204-211.
- [90] V.P. Haribal, F. He, A. Mishra, F. Li, Iron-Doped BaMnO<sub>3</sub> for Hybrid Water Splitting and Syngas Generation. *ChemSusChem.* 10 (2017) 3402-3408.
- [91] M.T. Curran, J.R. Kitchin, Effects of Concentration, Crystal Structure, Magnetism, and Electronic Structure Method on First-Principles Oxygen Vacancy Formation Energy Trends in Perovskites. *J. Phys. Chem. C.* 118 (2014) 28776-28790.
- [92] F.N. Ridha, M.A. Duchesne, X. Lu, D.Y. Lu, D. Filippou, R.W. Hughes, Characterization of an ilmenite ore for pressurized chemical looping combustion. *Appl. Energ.* 163 (2016) 323-333.
- [93] H.C. Zhou, J.R. Long, O.M. Yaghi, Introduction to metal-organic frameworks. *Chem Rev.* 112 (2) (2012) 673-4.
- [94] J.M. Yu, L.H. Xie, J.R. Li, Y.G. Ma, J.M. Seminario, P.B. Balbuena, CO<sub>2</sub> Capture and Separations Using MOFs: Computational and Experimental Studies. *Chem. Rev.* 117 (14) (2017) 9674-9754.
- [95] J.L.C. Rowsell, O.M. Yaghi, Metal-organic frameworks: a new class of porous materials. *Microporous Mesoporous Mater.* 73 (1-2) (2004) 3-14.
- [96] W.B. Xu, Q.Y. Ding, P.P. Sang, J. Xu, Z.M. Shi, L.M. Zhao, Y.H. Chi, W.Y. Guo, Effect of Modified Metal Center in Ligand for CO<sub>2</sub> Capture in Novel Zr-Based Porphyrinic Metal-Organic Frameworks: A Computational Investigation. *J. Phys. Chem. C.* 119 (38) (2015) 21943-21951.
- [97] A. Torrisi, R.G. Bell, C. Mellot-Draznieks, Functionalized MOFs for Enhanced CO<sub>2</sub> Capture. *Cryst. Growth Des.* 10 (7) (2010) 2839-2841.
- [98] S. Keskin, T.M. van Heest, D.S. Sholl, Can Metal-Organic Framework Materials Play a Useful Role in Large-Scale Carbon Dioxide Separations? *Chemsuschem.* 3 (8) (2010) 879-891.
- [99] D. Frenkel, B. Smit, *Understanding molecular simulation: from algorithms to applications*. Elsevier: 2001; Vol. 1.
- [100] M. Fischer, R.G. Bell, Influence of Zeolite Topology on CO<sub>2</sub>/N<sub>2</sub> Separation Behavior: Force-Field Simulations Using a DFT-Derived Charge Model. *J. Phys. Chem. C.* 116 (50) (2012) 26449-26463.
- [101] T.M. Becker, J. Heinen, D. Dubbeldam, L.C. Lin, T.J.H. Vugt, Polarizable Force Fields for CO<sub>2</sub> and CH<sub>4</sub> Adsorption in M-MOF-74. *J. Phys. Chem. C.* 121 (8) (2017) 4659-4673.
- [102] S. Keskin, J. Liu, R.B. Rankin, J.K. Johnson, D.S. Sholl, Progress, opportunities, and challenges

for applying atomically detailed modeling to molecular adsorption and transport in metal–organic framework materials. *Ind. Eng. Chem. Res.* 48 (5) 2355-2371.

[103] N.A. Ramsahye, G. Maurin, S. Bourrelly, P. Llewellyn, T. Loiseau, G. Ferey, Charge distribution in metal organic framework materials: transferability to a preliminary molecular simulation study of the CO<sub>2</sub> adsorption in the MIL-53 (Al) system. *Phys. Chem. Chem. Phys.* 9 (9) (2007) 1059-1063.

[104] J. Hu, Y. Liu, J. Liu, C. Gu, D. Wu, High CO<sub>2</sub> adsorption capacities in UiO type MOFs comprising heterocyclic ligand. *Microporous Mesoporous Mater.* 256 (2018) 25-31.

[105] D.D. Borges, P. Normand, A. Permiakova, R. Babarao, N. Heymans, D.S. Galvao, C. Serre, G. De Weireld, G. Maurin, Gas Adsorption and Separation by the Al-Based Metal-Organic Framework MIL-160. *J. Phys. Chem. C.* 121 (48) (2017) 26822-26832.

[106] Y. Liu, J. Liu, M. Chang, C.G. Zheng, Theoretical studies of CO<sub>2</sub> adsorption mechanism on linkers of metal-organic frameworks. *Fuel.* 95 (1) (2012) 521-527.

[107] J.M. Yu, P.B. Balbuena, Water Effects on Postcombustion CO<sub>2</sub> Capture in Mg-MOF-74. *J. Phys. Chem. C.* 117 (7) (2013) 3383-3388.

[108] D. Nazarian, J.S. Camp, Y.G. Chung, R.Q. Snurr, D.S. Sholl, Large-Scale Refinement of Metal-Organic Framework Structures Using Density Functional Theory. *Chem. Mater.* 29 (6) (2017) 2521-2528.

[109] H. Demir, J.A. Greathouse, C.L. Staiger, J.J. Perry, M.D. Allendorf, D.S. Sholl, DFT-based force field development for noble gas adsorption in metal organic frameworks. *J. Mater. Chem. A.* 3 (46) (2015) 23539-23548.

[110] A.K. Rappé, C.J. Casewit, K. Colwell, W.A. Goddard III, W. Skiff, a full periodic table force field for molecular mechanics and molecular dynamics simulations. *J. Am. Chem. Soc.* 114 (25) 10024-10035.

[111] E. Haldoupis, J. Borycz, H. Shi, K.D. Vogiatzis, P. Bai, W.L. Queen, L. Gagliardi, J.I. Siepmann, Ab Initio Derived Force Fields for Predicting CO<sub>2</sub> Adsorption and Accessibility of Metal Sites in the Metal–Organic Frameworks M-MOF-74 (M = Mn, Co, Ni, Cu). *J. Phys. Chem. C.* 119 (28) (2015) 16058-16071.

[112] R. Poloni, K. Lee, R.F. Berger, B. Smit, J.B. Neaton, Understanding Trends in CO<sub>2</sub> Adsorption in Metal-Organic Frameworks with Open-Metal Sites. *J. Phys. Chem. Lett.* 5 (5) (2014) 861-865.

[113] L. Vanduyfhuys, T. Verstraelen, M. Vandichel, M. Waroquier, V. Van Speybroeck, Ab Initio Parametrized Force Field for the Flexible Metal-Organic Framework MIL-53(Al). *J Chem Theory Comput.* 8 (9) (2012) 3217-31.

[114] P.D.-O.V.A. Roberts, V. Osguthorpe, D. Wolff, M. Genest, A. Hagler, Structure and Energetics of Ligand Binding to Proteins: Escherichia coli Dihydrofolate Reductase-Trimethoprim, A Drug-Receptor System. *PROTEINS: Structure, Function, and Genetics.* 4 31-47.

[115] J. Lange, F.G. de Souza, M. Nele, F.W. Tavares, I.S.V. Segtovich, G.C.Q. da Silva, J.C. Pinto, Molecular Dynamic Simulation of Oxaliplatin Diffusion in Poly(lactic acid-co-glycolic acid). Part A: Parameterization and Validation of the Force-Field CVFF. *Macromol. Theory Simul.* 25 (1) (2016) 45-62.

[116] M. Pera-Titus, Porous Inorganic Membranes for CO<sub>2</sub> Capture: Present and Prospects. *Chem. Rev.* 114 (2) (2014) 1413-1492.

[117] N. Du, H.B. Park, G.P. Robertson, M.M. Dal-Cin, T. Visser, L. Scoles, M.D. Guiver, Polymer nanosieve membranes for CO<sub>2</sub> capture applications. *Nature Materials.* 10 (2011) 372-375.

- [118] D.S. Sholl, Y.H. Ma, Dense Metal Membranes for the Production of High-Purity Hydrogen. *MRS Bulletin*. 31 (10) (2006) 770-773.
- [119] P. Kamakoti, D.S. Sholl, A comparison of hydrogen diffusivities in Pd and CuPd alloys using density functional theory. *J. Membrane Sci.* 225 (1) (2003) 145-154.
- [120] C. Ling, L. Semidey-Flecha, D.S. Sholl, First-principles screening of PdCuAg ternary alloys as H<sub>2</sub> purification membranes. *J. Membrane Sci.* 371 (1) (2011) 189-196.
- [121] N. Chandrasekhar, D.S. Sholl, Quantitative computational screening of Pd-based intermetallic membranes for hydrogen separation. *J. Membrane Sci.* 453 (2014) 516-524.
- [122] H. Zhang, X. He, M. Zhao, M. Zhang, L. Zhao, X. Feng, Y. Luo, Tunable hydrogen separation in sp-sp<sup>2</sup> hybridized carbon membranes: a first-principles prediction. *J. Phys. Chem. C*. 116 (31) (2012) 16634-16638.
- [123] C. Cazorla, S.A. Shevlin, Z.X. Guo, Calcium-Based Functionalization of Carbon Materials for CO<sub>2</sub> Capture: A First-Principles Computational Study. *J. Phys. Chem. C*. 115 (22) (2011) 10990-10995.
- [124] M. Ostwal, R.P. Singh, S.F. Dec, M.T. Lusk, J.D. Way, 3-Aminopropyltriethoxysilane functionalized inorganic membranes for high temperature CO<sub>2</sub>/N<sub>2</sub> separation. *J. Membrane Sci.* 369 (1) (2011) 139-147.
- [125] T. Wu, Q. Xue, C. Ling, M. Shan, Z. Liu, Y. Tao, X. Li, Fluorine-Modified Porous Graphene as Membrane for CO<sub>2</sub>/N<sub>2</sub> Separation: Molecular Dynamic and First-Principles Simulations. *J. Phys. Chem. C*. 118 (14) (2014) 7369-7376.
- [126] M. Benzaqui, R.S. Pillai, A. Sabetghadam, V. Benoit, P. Normand, J. Marrot, N. Menguy, D. Montero, W. Shepard, A. Tissot, Revisiting the Aluminum Trimesate-Based MOF (MIL-96): From Structure Determination to the Processing of Mixed Matrix Membranes for CO<sub>2</sub> Capture. *Chem. Mater.* 29 (24) (2017) 10326-10338.
- [127] S. Keskin, D.S. Sholl, Assessment of a Metal-Organic Framework Membrane for Gas Separations Using Atomically Detailed Calculations: CO<sub>2</sub>, CH<sub>4</sub>, N<sub>2</sub>, H<sub>2</sub> Mixtures in MOF-5. *Ind. Eng. Chem. Res.* 48 (2) (2009) 914-922.
- [128] P. Rochana, K. Lee, J. Wilcox, Nitrogen Adsorption, Dissociation, and Subsurface Diffusion on the Vanadium (110) Surface: A DFT Study for the Nitrogen-Selective Catalytic Membrane Application. *J. Phys. Chem. C*. 118 (8) (2014) 4238-4249.
- [129] Y. Wang, Q. Yang, J. Li, J. Yang, C. Zhong, Exploration of nanoporous graphene membranes for the separation of N<sub>2</sub> from CO<sub>2</sub>: a multi-scale computational study. *Phys. Chem. Chem. Phys.* 18 (12) (2016) 8352-8358.
- [130] Y. Wang, Q. Yang, C. Zhong, J. Li, Graphene-like Poly(triazine imide) as N<sub>2</sub>-Selective Ultrathin Membrane for Postcombustion CO<sub>2</sub> Capture. *J. Phys. Chem. C*. 120 (50) (2016) 28782-28788.
- [131] P. Gomez-Alvarez, S. Calero, Highly selective zeolite topologies for flue gas separation. *Chem. Eur. J.* 22 (52) (2016) 18705-18708.
- [132] D. Bonenfant, M. Kharoune, P. Niquette, M. Mimeault, R. Hausler, Advances in principal factors influencing carbon dioxide adsorption on zeolites. *Sci Technol Adv Mater.* 9 (1) (2008) 013007.
- [133] T. Ho Viet, L. Grajciar, P. Nachtigall, O. Bludsky, C. Otero Arean, E. Frydova, R. Bulanek, Adsorption of CO<sub>2</sub> in FAU zeolites: Effect of zeolite composition. *Catal. Today*. 227 (2014) 50-56.
- [134] O. Bludsky, M. Rubes, P. Soldan, P. Nachtigall, Investigation of the benzene-dimer potential energy surface: DFT/CCSD(T) correction scheme. *J Chem Phys.* 128 (11) (2008) 114102.
- [135] M. Fischer, R.G. Bell, A dispersion-corrected density-functional theory study of small molecules adsorbed in alkali-exchanged chabazites. *Z. Krist.-Cryst. Mater.* 228 (3) (2013) 124-133.


- [136] A. Tot, S. Armakovic, S. Armakovic, S. Gadzuric, M. Vranes, Kosmotropism of newly synthesized 1-butyl-3-methylimidazolium taurate ionic liquid: Experimental and computational study. *J. Chem. Thermodyn.* *94* (2016) 85-95.
- [137] J.A. Steckel, Ab Initio Calculations of the Interaction between CO<sub>2</sub> and the Acetate Ion. *J. Phys. Chem. A.* *116* (47) (2012) 11643-11650.
- [138] D. Valencia-Marquez, A. Flores-Tlacuahuac, L. Ricardez-Sandoval, A controllability analysis of a pilot-scale CO<sub>2</sub> capture plant using ionic liquids. *Aiche J.* *62* (9) (2016) 3298-3309.
- [139] D. Valencia-Marquez, A. Flores-Tlacuahuac, L. Ricardez-Sandoval, Technoeconomic and Dynamical Analysis of a CO<sub>2</sub> Capture Pilot-Scale Plant Using Ionic Liquids. *Ind. Eng. Chem. Res.* *54* (45) (2015) 11360-11370.
- [140] H. Sun, B. Qiao, D. Zhang, C. Liu, Structure of 1-butylpyridinium tetrafluoroborate ionic liquid: quantum chemistry and molecular dynamic simulation studies. *J. Phys. Chem. A.* *114* (11) (2010) 3990-3996.
- [141] S. Aparicio, M. Atilhan, A Computational Study on Choline Benzoate and Choline Salicylate Ionic Liquids in the Pure State and After CO<sub>2</sub> Adsorption. *J. Phys. Chem. B.* *116* (30) (2012) 9171-9185.
- [142] S. Aparicio, M. Atilhan, M. Khraisheh, R. Alcalde, Study on hydroxylammonium-based ionic liquids. I. Characterization. *J Phys Chem B.* *115* (43) (2011) 12473-86.
- [143] R. Peverati, D.G. Truhlar, Improving the Accuracy of Hybrid Meta-GGA Density Functionals by Range Separation. *J. Phys. Chem. Lett.* *2* (21) (2011) 2810-2817.
- [144] O.A. Vydrov, T. Van Voorhis, Nonlocal van der Waals density functional: The simpler the better. *J. Chem. Phys.* *133* (24) (2010) 244103.
- [145] K. Lee, É.D. Murray, L. Kong, B.I. Lundqvist, D.C. Langreth, Higher-accuracy van der Waals density functional. *Phys. Rev. B.* *82* (8) (2010).
- [146] G.B. Damas, A.B.A. Dias, L.T. Costa, A Quantum Chemistry Study for Ionic Liquids Applied to Gas Capture and Separation. *J. Phys. Chem. B.* *118* (30) (2014) 9046-9064.
- [147] T.C. Lourenco, M.F. Coelho, T.C. Ramalho, D. van der Spoel, L.T. Costa, Insights on the solubility of CO<sub>2</sub> in 1-ethyl-3-methylimidazolium bis(trifluoromethylsulfonyl) imide from the microscopic point of view. *Environ Sci Technol.* *47* (13) (2013) 7421-9.
- [148] G. Garcia, M. Atilhan, S. Aparicio, Assessment of DFT methods for studying acid gas capture by ionic liquids. *Phys. Chem. Chem. Phys.* *17* (40) (2015) 26875-26891.
- [149] J.D. Chai, M. Head-Gordon, Long-range corrected hybrid density functionals with damped atom-atom dispersion corrections. *Phys Chem Chem Phys.* *10* (44) (2008) 6615-20.
- [150] S. Grimme, Semiempirical GGA-type density functional constructed with a long-range dispersion correction. *J Comput Chem.* *27* (15) (2006) 1787-99.
- [151] A. Mondal, S. Balasubramanian, A Refined All-Atom Potential for Imidazolium-Based Room Temperature Ionic Liquids: Acetate, Dicyanamide, and Thiocyanate Anions. *J. Phys. Chem. B.* *119* (34) (2015) 11041-11051.
- [152] J.N. Canongia Lopes, J. Deschamps, A.A. Pádua, Modeling ionic liquids using a systematic all-atom force field. *J. Phys. Chem. B.* *108* (6) (2004) 2038-2047.
- [153] J.N. Canongia Lopes, J. Deschamps, A.A. Pádua, Modeling ionic liquids using a systematic all-atom force field-Additions and corrections. *J. Phys. Chem. B.* *108* (30) (2004) 11250.
- [154] J.N. Canongia Lopes, A.A. Pádua, Molecular Force Field for Ionic Liquids Composed of Triflate or Bistriflylimide Anions. *J. Phys. Chem. B.* *108* (43) 16893-16898.

- [155] B. Gao, J.X. Zhao, Q.H. Cai, X.G. Wang, X.Z. Wang, Doping of Calcium in C-60 Fullerene for Enhancing CO<sub>2</sub> Capture and N<sub>2</sub>O Transformation: A Theoretical Study. *J. Phys. Chem. A*. 115 (35) (2011) 9969-9976.
- [156] S.C. Zhuo, Y.M. Huang, J. Hu, H.L. Liu, Y. Hu, J.W. Jiang, Computer simulation for adsorption of CO<sub>2</sub>, N<sub>2</sub> and flue gas in a mimetic MCM-41. *J. Phys. Chem. C*. 112 (30) (2008) 11295-11300.
- [157] A. Zukal, J. Jagiello, J. Mayerova, J. Cejka, Thermodynamics of CO<sub>2</sub> adsorption on functionalized SBA-15 silica. NLDFT analysis of surface energetic heterogeneity. *Phys. Chem. Chem. Phys.* 13 (34) (2011) 15468-15475.
- [158] T. Nittaya, P.L. Douglas, E. Croiset, L.A. Ricardez-Sandoval, Dynamic modelling and control of MEA absorption processes for CO<sub>2</sub> capture from power plants. *Fuel*. 116 (2014) 672-691.
- [159] Z. He, L.A. Ricardez-Sandoval, Dynamic modelling of a commercial-scale CO<sub>2</sub> capture plant integrated with a natural gas combined cycle (NGCC) power plant. *Int. J. Greenh. Gas Con.* 55 (2016) 23-35.
- [160] J. Gaspar, L.R. Sandoval, J.B. Jørgensen, P.L. Fosbøl, Design, Economics and Parameter Uncertainty in Dynamic Operation of Post-combustion CO<sub>2</sub> Capture Using Piperazine (PZ) and MEA. *Energy Procedia*. 114 (2017) 1444-1452.
- [161] J. Gaspar, L. Ricardez-Sandoval, J.B. Jørgensen, P.L. Fosbøl, Controllability and flexibility analysis of CO<sub>2</sub> post-combustion capture using piperazine and MEA. *Int. J. Greenh. Gas Con.* 51 (2016) 276-289.
- [162] Z. He, M.H. Sahraei, L.A. Ricardez-Sandoval, Flexible operation and simultaneous scheduling and control of a CO<sub>2</sub> capture plant using model predictive control. *Int. J. Greenh. Gas Con.* 48 (2016) 300-311.
- [163] T. Islamoglu, S. Behera, Z. Kahveci, T.D. Tessema, P. Jena, H.M. El-Kaderi, Enhanced Carbon Dioxide Capture from Landfill Gas Using Bifunctionalized Benzimidazole-Linked Polymers. *ACS Appl. Mater. Interfaces*. 8 (23) (2016) 14648-14655.
- [164] L. Liu, W.L. Fan, X. Zhao, H.G. Sun, P. Li, L.M. Sun, Surface Dependence of CO<sub>2</sub> Adsorption on Zn<sub>2</sub>GeO<sub>4</sub>. *Langmuir*. 28 (28) (2012) 10415-10424.
- [165] R. Hammami, H. Batis, C. Minot, Combined experimental and theoretical investigation of the CO<sub>2</sub> adsorption on LaMnO<sub>3+y</sub> perovskite oxide. *Surf. Sci.* 603 (20) (2009) 3057-3067.
- [166] Y.X. Pan, C.J. Liu, Q.F. Ge, Adsorption and Protonation Of CO<sub>2</sub> on Partially Hydroxylated gamma-Al<sub>2</sub>O<sub>3</sub> Surfaces: A Density Functional Theory Study. *Langmuir*. 24 (21) (2008) 12410-12419.
- [167] K.R. Hahn, M. Iannuzzi, A.P. Seitsonen, J. Hutter, Coverage Effect of the CO<sub>2</sub> Adsorption Mechanisms on CeO<sub>2</sub>(111) by First Principles Analysis. *J. Phys. Chem. C*. 117 (4) (2013) 1701-1711.
- [168] H.J. Jang, C.H. Lee, S. Kim, S.H. Kim, K.B. Lee, Hydrothermal synthesis of K<sub>2</sub>CO<sub>3</sub>-promoted hydrotalcite from hydroxide-form precursors for novel high-temperature CO<sub>2</sub> sorbent. *ACS Appl Mater Interfaces*. 6 (9) (2014) 6914-9.
- [169] M.T. Curnan, J.R. Kitchin, Effects of concentration, crystal structure, magnetism, and electronic structure method on first-principles oxygen vacancy formation energy trends in perovskites. *J. Phys. Chem. C*. 118 (49) (2014) 28776-28790.

**Table 1 Materials commonly used in CCS technologies**

<b>Type</b>	<b>Technology</b>	<b>Commonly used materials</b>	<b>Features</b>
Oxygen carrier	Oxy-combustion (chemical looping combustion)	Fe <sub>2</sub> O <sub>3</sub> [22], NiO[23], ilmenite[24]	Low-cost, energy efficient, inactivation by impurity production

Metal organic framework	Pre-combustion; post-combustion; oxy-combustion	Cu-BTC[25], ZIFs[26], MIL-102[27]	Chemical diversity, high modulability, large surface area, expensive
Membrane	Pre-combustion; post-combustion; oxy-combustion	Pd-alloys[28], Modified-graphenes[29], MOFs[30]	Flexible, energy efficient, tradeoff between CO <sub>2</sub> permeability and selectivity
Zeolite	Pre-combustion; post-combustion;	Na-A zeolite[31], alkaline zeolite[32]	Molecular sieving property, high capacity under moderate conditions , high regeneration temperatures
Ionic liquid	Pre-combustion; post-combustion	amino acid ionic liquids[33], 1-ethyl-3-methylimidazoliu m cation based liquid[34], tetrabutylphosphonium glycinate[35]	High thermal stability, high modulability, low rate of adsorption
Porous carbon	Pre-combustion	nanotube[36], functionalized carbon[37], graphene[38]	Cheap, large adsorption capacity under high pressures, low selectivity,
Mesoporous silica nanoparticle	Pre-combustion	SBA-15[39], MCM-41[40]	Tunable surface, cheap
Amine-based solvent	Post-combustion;	mono-ethanolamine(MEA), piperazine[41], 2-amino-2methyl-1-propan ol[42]	Commercially mature, high energy penalty to regenerate

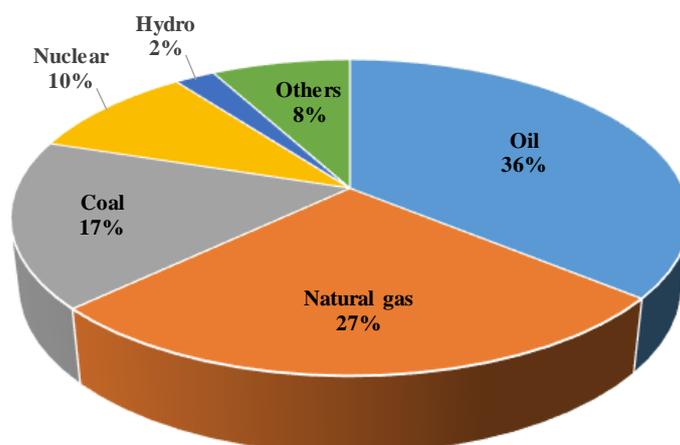

**Fig.1** Contribution of fossil fuels to the overall energy supply in 2016

ACCEPTED MAN



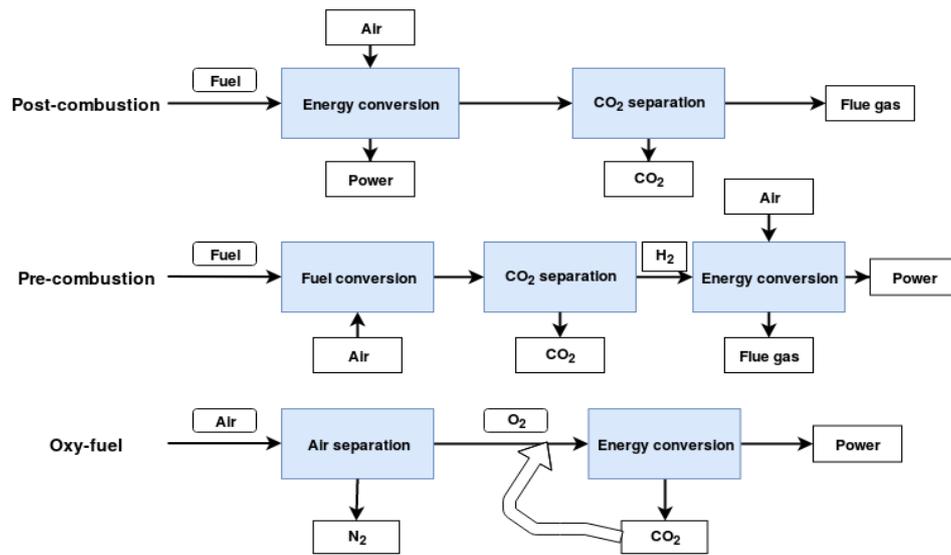


Fig.2 Process scheme of CO<sub>2</sub> capture technologies

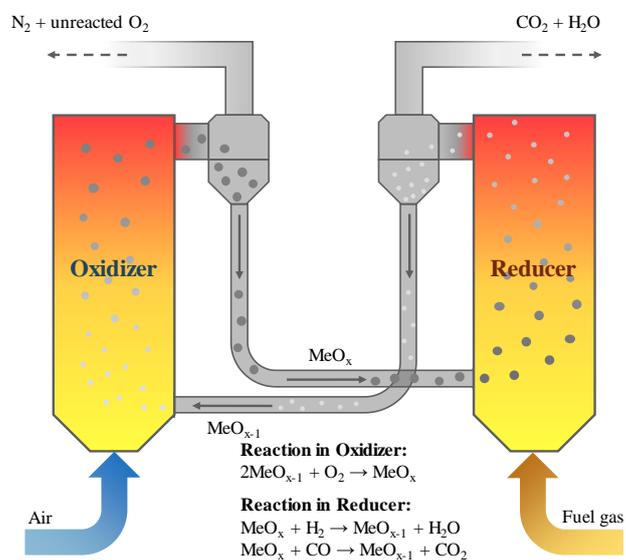


(a) Reaction scheme of a type I CLC process

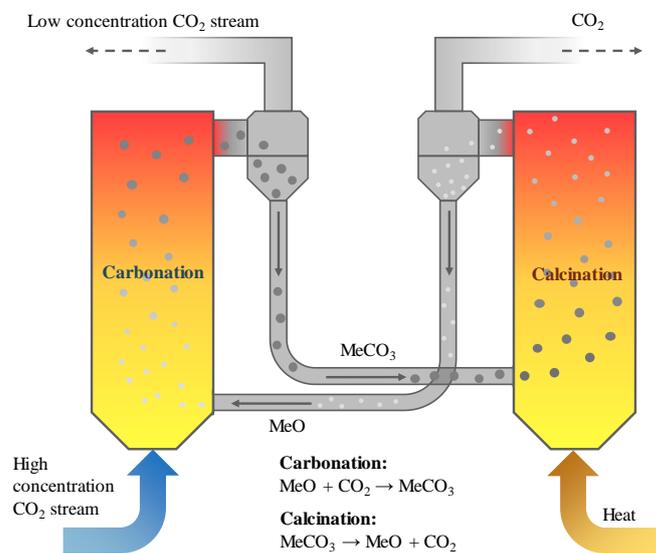

(b) Reaction scheme of type II CLC process

**Fig. 3** Reaction schemes of CLC processes

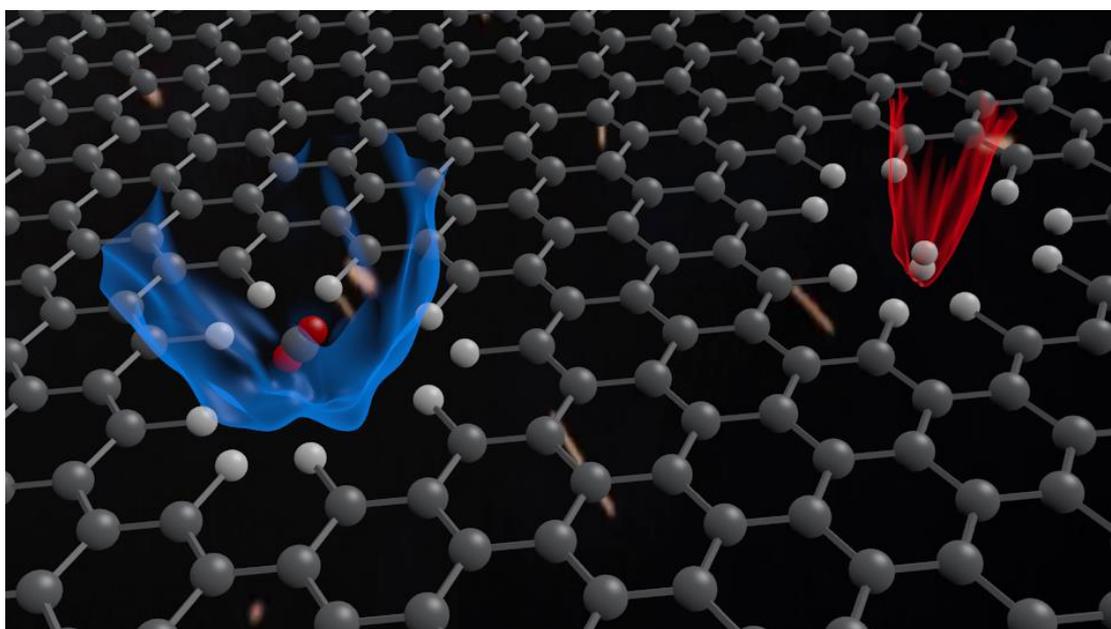

**Fig.4** CO<sub>2</sub> and H<sub>2</sub> penetrate through HP13 membrane